AD-A022 099

SOLID REACTANTS FOR FLUORINE GAS GENERATORS

C. E. Fogle, et al

United Technologies Corporation

Prepared for:

Naval Surface Weapons Center

15 March 1976

085122

CSD 2564-FR

SOLID REACTANTS FOR FLUORINE GAS GENERATORS

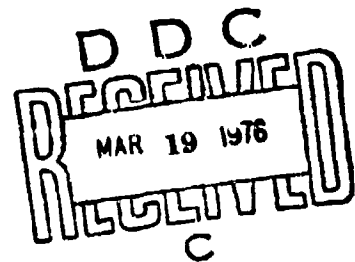C.E. Fogle

J.D. Breazeale

United Technologies Corporation

Chemical Systems Division

P.O. Box 358

Sunnyvale, Ca. 94088

D D C

MAR 19 1976

C

15 March 1976

Final Report for Period 2 June 1975 — 2 February 1976

Prepared for

NAVAL SURFACE WEAPONS CENTER

White Oak Laboratory

Silver Spring, Maryland 20910

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Solid Reactants for Fluorine Gas Generation		5. TYPE OF REPORT & PERIOD COVERED Final Report 2 June 75 to 2 Feb 76
		6. PERFORMING ORG. REPORT NUMBER CSD 2564-FR
7. AUTHOR(s) C. E. Fogle J. D. Breazeale		8. CONTRACT OR GRANT NUMBER(s) N60921-75-C-0224
9. PERFORMING ORGANIZATION NAME AND ADDRESS		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 233-0132-75
11. CONTROLLING OFFICE NAME AND ADDRESS United Technologies Corporation Chemical Systems Division P.O. Box 358/Sunnyvale, CA 94088		12. REPORT DATE 15 March 1976
		13. NUMBER OF PAGES 103
14. MONITORING AGENCY NAME & ADDRESS(if different from Controlling Office) Naval Surface Weapons Center White Oak Laboratory Silver Spring, MD 20910 Code WD-04		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE

16. DISTRIBUTION STATEMENT (of this Report)

Approved for public release: distribution unlimited.

17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)

18. SUPPLEMENTARY NOTES

19. KEY WORDS (Continue on reverse side if necessary and identify by block number)

Fluorine Source
Gas Generator
Solid Propellant
Fluorine Generator
Lasers

20. ABSTRACT (Continue on reverse side if necessary and identify by block number)

A program has been conducted to explore the possibility of using solid reactants, other than those currently under consideration, for the preparation of fluorine equivalent gas (F, F_2, or NF_3) and to evaluate the potential of promising candidates. A list of 32 candidates was compiled which was reduced to 3, $KBrF_6$, $KClF_4$, and $LiMnF_5$, by applying pre-established selection criteria based on toxicity, cost, safety, vapor pressure or melting point, and others.

DD $_{1\ JAN\ 73}^{FORM}$ 1473   EDITION OF 1 NOV 65 IS OBSOLETE

20. (continued)

Excellent properties and performance were obtained from a formulation based on $KBrF_6$ yielding approximately 13% by weight equivalent fluorine (18 percent by weight active fluorine) with a potential of over 25 percent active fluorine through composition variation. This approach was abandoned owing to the lack of information related to the effect of the species BrF on HF-DF laser output. Similarly, although equally good properties and performance could be obtained, $KClF_4$ formulation evaluation was discontinued when it became known that ClF has a deleterious effect. The third candidate, $LiMnF_5$, offers the possibility of the production of pure fluorine albeit at relatively low yield (about 10 weight percent) and investigations of its formulations have been pursued.

SUMMARY

A series of available or known solid reactants capable of generating fluorine when combined with fuels was identified and examined during the course of the program.

An extensive literature review combined with a thermochemical evaluation procedure defined candidates with labile fluorine that were subsequently screened as to acceptability in meeting specified requirements. A series of 32 candidate fluorine reactants was included in the reactant screening and rating operations. The parameters that had major influence on reactant acceptability during this screening operation were stability, safety, and cost.

A series of five reactants was selected for experimental evaluation based on the reactant ratings. The compounds were $NOBrF_4$, $(NO)_2MnF_6$, $KBrF_6$, $KClF_4$, and $LiMnF_5$. The first two reactants, $NOBrF_4$ and $(NO)_2MnF_6$, were eliminated from consideration at an early stage because of the low fluorine yield of $(NO)_2MnF_6$ and the expected detrimental influence of NOF and bromine products on laser prformance in the case of $NOBrF_4$. The two interhalogen derivatives, $KBrF_6$ and $KClF_4$, were carried through small-scale grain testing (10 to 20 g). Test data showed the $KBrF_6/Mg_3N_2$ and $KClF_4/AlN$ reactant systems to be most amenable to ignition and combustion in the scale tested. Studies of these two reactant systems were discontinued based on the anticipated detrimental effects of BrF and ClF on laser performance.

Work on $LiMnF_5$ was conducted based on prediction of fluorine as the only gaseous product with other products forming a sintered residue. Ignition and combustion of various $LiMnF_5$ and fuel reactant systems were difficult to achieve on the scale tested. The most promising candidate based on the grains tested consisted of a $LiMnF_5/Mg$ formulation.

An exploratory analysis and design of a fluorine gas generator system were developed using the $LiMnF_5/Mg$ reactant system parameters as input. The primary area of uncertainty was in the ignition train design.

PREFACE

iv

CONTENTS

FIGURES

TABLES

INTRODUCTION

This document describes the investigations performed under NSWC contract No. N60921-75-C-0224, "Solid Reactants for Fluorine Generation." The overall objectives of the program were to select, by approved screening and selection criteria, and to evaluate by tests and analysis, solid reactants and approaches capable of producing F, F_2, or NF_3 at weight yields corresponding to 10% equivalent fluorine with an ultimate goal of 25% equivalent fluorine. Furthermore, the reactant systems and approaches selected should be capable of producing an exhaust containing minimum levels of contaminants or particles and the system should be scalable to produce 0.25 lb of fluorine per second for up to 5 sec duration.

Principal operational constraints in development of a DF chemical laser are the storing, handling, and safety of the reactants. These constraints emphasized the desirability of solid gas generators to produce the gaseous reactants needed for HF/DF lasers. With demonstrated practical generation of H_2 and D_2 from solid formulations and since stored helium, nitrogen, or nitrogen-generating formulations can be used as the diluent gas source, the primary remaining problem area is that of a suitable fluorine source.

The hazardous nature and physical properties of fluorine combine to make its storage in the elemental form a formidable undertaking if substantial quantities are to be stored for extended periods. The problems of corrosivity during the storage period, the potential of boiloff or leakage of the liquid phase when employed as a cryogenic reagent, and the need to supply a pressurization subsystem are drawbacks to liquid fluorine. The inherent storability of solid reactants makes the approach of solid grains for fluorine generation attractive, and has been the primary impetus for work in this area.

Although several fluorine-generating formulations have been characterized to date on a laboratory scale, there is currently no fully developed composition based on available reactants which produces F, F_2, or NF_3 as combustion products. Among the reactants which have been investigated

5

as fluorine generation sources are the xenon fluorides, XeF_2 and XeF_4, and the NF_4^+ salts, NF_4BF_4 and NF_4SbF_6. The xenon fluorides exhibit marginal stability characteristics, particularly for Navy usage. The higher fluorine content compounds, NF_4BF_4 and NF_4SbF_6, are presently not available at reasonable cost in quantities sufficient for large-scale operations.

The program reported herein is an investigation of alternative approaches for generation of gaseous F, F_2, and NF_3 by means of solid reactants based on available, relatively inexpensive ingredients. The availability and low cost requirements were imposed to provide a trade-off option to the higher cost tetrafluoroammonium salts. In addition, constraints on the gaseous product composition were imposed such that it would be acceptable for DF laser operation. Finally, the requirements included practical guidelines relating to handling and safety.

The program developed to meet these objectives was divided into three consecutive tasks: task 1, screening and selection of reactants and approaches; task 2, characterization and testing of the selected reactant systems; and task 3, scalability testing and supporting analysis. The program plan provided for specification of five candidate reactants at the end of screening studies of task 1, selection of three candidates to be evaluated during the testing effort of task 2, and up to two candidates for the task 3 scalability testing and supporting analysis.

Synthesis studies performed as part of the IR&D program yielded a portion of the reactant materials used in the task 2 efforts. For completeness, the results of these studies have been included in this report where appropriate.

Several requirements for a gas generator producing predominantly gaseous fluorine can be defined. A primary guideline is production of gas generator products that approach, or match, the composition of gases currently being used in laser operations (i.e., fluorine, fluorine-helium, or fluorine-nitrogen mixtures). Achievement of this guideline allows more ready transition from lasers employing gaseous fluorine to solid generator operated lasers.

Throughout the program, a set of requirements was considered that imposed limits on acceptability of various physical, chemical, and economic properties of candidate reactants. These requirements, while subjective in certain areas, were intended to ensure that the final reactant systems (fluorine gas generators) would have utility in an end-item application. The minimum requirements that need to be satisfied for both the fluorine reactants and reactant systems are as follows:

A. Yield of fluorine (as F, F_2, and NF_3) of 10 weight percent (minimum) to 25 weight percent (goal).

B. Reactants are stable solids (and nonvolatile) at temperatures up to 50 C.

C. Reactants are available from commercial sources or can be synthesized by practical synthesis routes.

D. Once ignited, reactant systems sustain a controlled combustion.

E. Minimum concentrations of undesirable or unacceptable gases are produced upon combustion:

(1) Acceptable - N_2, O_2, He, Ar, CF_4, and SF_6

(2) Undesirable - HF, DF, CO_2, COF_2, SO_2F_2, and ClF_3

(3) Unacceptable - Fluorine reactive gases

F. Reactants and fluorine gas generator formulations have normal handling characteristics:

(1) Low sensitivity to impact, friction, and spark

(2) Autoignition temperature (AIT) in excess of 120 C

(3) Low toxicity of reactants

(4) Storable at normal temperatures

7

(5) Capable of being processed in large scale.

G.   Particulate matter can be removed from generated gas.

Of the noted requirements, those having the greatest impact on the
selection of reactants were the fluorine content (item A) and availability
(item C), whereas the selection of reactant systems for evaluation was
constrained primarily by the presence of other gases in the products (item E)
and achieving sustained combustion (item D). The last item, elimination of
condensed solids from the exhaust, is dependent upon the formulation and end
use approach.

The three basic approaches to producing a solids-free exhaust in the
fluorine gas generators were all considered in the course of the selection
process conducted in this program. The first approach follows conventional
gas generator technology by formulation of compositions whose products are
all gaseous, e.g., the early formulations of NF_4BF_4 with
tetrafluoroethylene[1] are typical of this approach. This type of
formulation has the advantage of not requiring separation of condensed
products from the gas phase but tends to produce excessive gaseous
contaminant levels. The second approach considered in the program is an
adaptation of the well-established chlorate candle technology[2] to develop
formulations that produce a sintered solid under certain definable
conditions. Previous studies have shown that, provided the ratio of the
liquid-to-solid phases is controlled, good separation of gases from the
condensed phases occurs. A small filtration unit normally has been required
to remove the last vestiges of condensed particles. Excessive amounts of a
liquid phase have been found to cause slumping problems on scale-up.[3] This
second type of generator generally provides a lower fluorine yield, based on
total gas generator weight, but produces a gaseous product with a higher
fluorine content. The use of the sintered residue approach for fluorine
generators has been reported in work using NF_4SbF_6[4] and NF_4BF_4[5]. The
third approach also allows formation of solid- or liquid-phase combustion
products but does not produce a sintered residue. In this approach, a
second subsystem is required to remove the condensed products. The
complexity of this subsystem is dependent upon the combustion temperature and

8

the quantities and physical characteristics of the condensed, and condensable, combustion products. This third type of system is potentially adaptable to an accumulator approach for multipulse operation.

The following sections present the overall approaches taken to evaluate alternative solid reactants for fluorine generators; the results of the theoretical, experimental, and design studies based on the selected approaches; and a discussion of the results.

TASK 1: SCREENING AND SELECTION OF CANDIDATE REACTANTS AND APPROACHES

The objective of this task was to survey potential fluorine source candidate reactants, subject these candidates to a set of approved screening criteria, and select and recommend the most appropriate reactants for subsequent testing. A reactants considered list was prepared to summarize the results of task 1. A minimum of five reactant systems was selected for consideration in the testing phase (task 2) which follows this section.

The initial step in the screening and selection process consisted of a thorough literature search, including the use of automated information retrieval services, for all compounds having a potential for release of at least a portion of their fluorine on thermal excitation. This literature search resulted in identification of in excess of 60 candidate compounds for later evaluation in the program. (Pertinent literature is listed in the bibliography as references 6 through 45.)

The stability of a selected set of gaseous fluorides was evaluated from thermodynamic considerations to serve as a guideline in the selection of materials which possess weakly bound fluorine or form species with weak bonds to fluorine and therefore decompose readily. The equilibrium decomposition temperature for these species, tabulated in table 1, was calculated as the temperature at which log K_p was approximately zero.

Temperature limitations were imposed on the evaluation by end-use application. In the case of a DF laser, the lower limit is that required to dissociate F_2, approximately 1300 K, while the upper limit is imposed by

9

TABLE 1.   RELATIVE STABILITY OF GASEOUS SPECIES CONTAINING FLUORINE

Species	Decomposition Reaction	Decomposition[a] Temperature, (K)
ClF_5	$ClF_5 \longrightarrow ClF_3 + F_2$	500
NOF_3	$2NOF_3 \longrightarrow N_2 + O_2 + 3F_2$	600
IF_7	$IF_7 \longrightarrow IF_5 + F_2$	600
NO_2F	$2NO_2F \longrightarrow N_2 + 2O_2 + F_2$	750
ClF_3	$ClF_3 \longrightarrow ClF + F_2$	800
NF_3	$2NF_3 \longrightarrow N_2 + 3F_2$	900
BrF_5	$BrF_5 \longrightarrow BrF_3 + F_2$	1000
NOF	$2NOF \longrightarrow N_2 + O_2 + F_2$	1200
F_2	$F_2 \longrightarrow 2F$	1300
BrF_3	$BrF_3 \longrightarrow BrF + F_2$	1500
SF_6	$SF_6 \longrightarrow SF_4 + F_2$	2100
IF_5	$IF_5 \longrightarrow IF_3 + F_2$	2600
SO_2F_2	$SO_2F_2 \longrightarrow SO_2 + F_2$	3500
PF_5	$PF_5 \longrightarrow PF_3 + F_2$	3800
SF_4	$SF_4 \longrightarrow S + 2F_2$	4100
SOF_2	$2SOF_2 \longrightarrow 2S + O_2 + 2F_2$	4500
PF_3	$PF_3 \longrightarrow PF + F_2$	>6000
CF_4	$CF_4 \longrightarrow C + 2F_2$	>6000
BF_3	$2BF_3 \longrightarrow 2B + 3F_2$	>6000
COF_2	$2COF_2 \longrightarrow 2C + O_2 + 2F_2$	>6000
ClF	$2ClF \longrightarrow Cl_2 + F_2$	>6000
BrF	$2BrF \longrightarrow Br_2 + F_2$	>6000
IF	$2IF \longrightarrow I_2 + F_2$	>6000
PF	$2PF \longrightarrow 2P + F_2$	>6000

[a] Temperature where $\log K_p$ is near zero.

10

nozzle processes or materials consideration and is of the order of 2500 K. Therefore, those species whose dissociation occurs at temperatures less than 2500 K will have the most utility in the application, whereas those species which decompose at higher temperatures will remain intact at operational temperatures and do not represent sources of available fluorine. The emphasis on the dissociation of species, especially into F atoms, arises from the energetics of the DF laser system which cause the overall system performance to suffer if even the energy of dissociation for F_2 must be supplied internally.

It is apparent from table 1 that fluorine bonded to nitrogen is available, since all nitrogen-bonded species (NOF_3, NOF, NO_2F, and NF_3) decompose below the operating temperature of the laser combustor. Conversely, boron, phosphorus, carbon, and sulfur are not desirable as fluorine carriers since their polyfluorides are stable above the operating temperature. Of the interhalogens, chlorine and bromine can be expected to dissociate to the monofluorides; however, iodine clearly would result in formation of IF_5 as a stable product gas. The relative stability of the gaseous fluorides then is reflected in the fluorine yield values of candidate reactants. Armed with this information, the fluorine-containing compounds collected in the literature review were subjected to a preliminary screening to eliminate those without labile fluorine. A value of 10 weight percent available fluorine was imposed as an absolute lower limit of acceptability; however, for use in operational systems, a more practical value of 20 weight percent was employed.

Reactants Considered List

The reactants considered list (RCL) was compiled from all the candidate materials which remained after the preliminary review. In addition, several of the current NF_4^+ candidates were included for comparison bringing the list to a total of 32 materials to be evaluated. The RCL was subdivided into a set of five tables according to the nature of the properties to be tabulated. The various tables, the data contained thereon, and the basic source of information are summarized in table 2. The individual tables making up the RCL are compiled in appendix A.

11

TABLE 2. REACTANTS CONSIDERED LIST

Table	Title	Data	Source
RCL-1	Fluorine yield of reactants	Weight percent F at 300, 1000, 1500, 2000 K and γ at 1500 K	Thermochemical calculations
RCL-2	Stability of reactants	Physical properties, ΔH_f°, decomposition temperature, chemical reactivity	Technical literature
RCL-3	Reactant availability and cost	Availability, synthesis routes, cost in 10-, 100-, 1000-, and 10,000-lb lots	Technical literature, chemical suppliers
RCL-4	Reactant safety	Reactivity with air, precursor and decomposition product toxicity	Technical literature
RCL-5	Reactant system performance	Weight percent F and γ for candidate formulations	Thermochemical calculations

Reactant Screening Procedure

The screening and selection process initially included the consideration
of three approaches to the reactant systems based on the nature of the
products of the generator. The first produces all gas products, the second
produces a condensed phase which is retained as a residue and an easily
filterable gas, while the third produces a gas with a relatively large
fraction of condensed phase e' .er entrained or formed during cooling.
During the course of the program, attention was directed toward the second
approach, i.e., reactants forming a sintered solid and a low solids content
gas.

To evaluate the relative merits of the candidate reactants and reactant
systems, a set of ranking criteria and weighting factors were established.
These are tabulated in table 3. Five categories were established with each
major category subdivided into related considerations.

The criteria incorporated those factors which would be expected to lead
to a reasonably priced solid reactant system capable of delivering an
adequate supply of fluorine gas free of excess contamination and with a
minimum of hazards associated with its manufacture and use. A major
consideration was the available fluorine content, initially of the reactant
itself but ultimately of the reactant system which will produce the gas.
This overall factor was given a weight of 25 out of a total of 100, divided
10 points for the reactant fluorine content and 15 points for gas generator
fluorine content. The acceptable lower limit was designated as 20 weight
percent for the reactant fluorine content and as 10 weight percent for the
gas generator fluorine content. This differential was established to account
for the consumption of reactant available fluorine by fuels incorporated in
the candidate formulations.

The availability of the reactants or precursors and well-established
synthesis routes were important considerations related to the cost of the
constituents of the gas generator. These factors were combined as the second
major criterion with a weighting factor of 20, divided equally between

13

TABLE 3. RANKING CRITERIA AND WEIGHTING FACTORS

Criterion	Weighting Factor	Value Limit
Available fluorine content	25	
Reactant fluorine content	(10)	>20 weight percent F
Gas generator fluorine content	(15)	>10 weight percent F
Availability and cost	20	
Availability	(10)	Synthesis established
Cost	(10)	<$10/g for 10 lb
Stability, toxicity, and safety	35	
Reactant stability	(10)	>50 C
Reactant and product toxicity	(10)	Noncumulative
Safety of reactant system	(15)	Impact > 10 kg-cm
Product contamination by particles or deactivating species	15	To be defined
Ignitibility and combustion stability	5	Ignition by hot wire

14

availability and cost. No definable limit was established for availability; a cost limit of less than $10 per gram in small scale was taken as a guideline.

Of vital concern was the safety, stability, and toxicity of the reactants, the processing characteristics of the reactant system and its stability as a gas generator. The third criterion of stability, toxicity, and safety was given a weighting factor of 35, the greatest weight of all criteria. This factor was subdivided into the three considerations with safety taking the predominant portion. This weighting was established based on previous safety constraints for shipboard operations. The acceptable lower limit of reactant stability was taken as 50 C (122 F). Reactants were ruled unacceptable if they or the products of combustion exhibited a chronic toxicity. A value of 10 kg-cm was established as the lower acceptable limit for impact sensitivity.

The degree of contamination of the product with solid particulate matter or with deactiving species would have a major impact on the value of candidate reactant systems in laser applications. This criterion was given a weighting factor of 15; however, since these parameters are difficult to define before test operations, this criterion had little effective impact on the selection process. Similarly, ignitability of the reactant system was also a factor to be considered in the system selection since a self-sustaining reaction must be initiated; however, determination of this criterion required extensive test data, not available on many reactants during screening.

The procedure used for the selection of the candidate reactants for ranking involved classification of the reactants as to acceptability in meeting the minimum requirements and those that were unacceptable on one basis or another. This classification is shown in table 4 for the 32 candidates. This tabulation was taken from the reactants considered list (appendix A) where the basis for the lack of acceptability is noted as an X on the RCL tables and, similarly, on the classification of reactants table. Those factors denoted by a parenthesized X were deemed marginal but this

15

TABLE 4. CLASSIFICATION OF REACTANTS

Reactant No.	Reactant Composition	Ref.	F, (weight percent)	Cost	Physical Properties	Reactivity/ Safety	Availability	Acceptable
1	NF_4BF_4	6	-	X	-	-	X	No
2	XeF_6	7	-	(X)	(X)	X	(X)	No
3	$2NOF \cdot XeF_6$	8	-	(X)	-	X	(X)	No
4	$KrF_2 \cdot XeF_6$	9	-	(X)	-	X	(X)	No
5	$NOClF_4$	10,11	-	-	X	-	-	No
6	$4XeF_6 \cdot MnF_4$	12	-	(X)	-	X	(X)	No
7	$4XeF_6 \cdot SnF_4$	13	-	(X)	-	X	(X)	No
8	$NOF \cdot XeOF_4$	14	-	(X)	(X)	X	(X)	No
9	$XeF_2 \cdot BrF_5$	15	-	(X)	X	-	(X)	No
10	$XeF_6 \cdot BF_3$	16	-	(X)	-	X	(X)	No
11	NF_4AsF_6	17,18,19	-	-	-	X	-	No
12	$(NO)_2MnF_6$	20	-	-	-	-	-	Yes
13	$KBrF_6$	21	-	-	-	-	-	Yes
14	$NF_3O \cdot SbF_5$	22,23	-	-	-	-	(X)	Yes
15	$NOBrF_4$	24	-	-	-	-	-	Yes
16	$XeF_2 \cdot XeF_4$	25,26	-	-	-	X	(X)	No
17	BrF_6AsF_6	27,28,29	-	-	-	X	-	No
18	$NOAsF_6$	44,45	-	-	-	X	-	No
19	NF_4SbF_6	33,34	-	-	-	-	-	Yes
20	$N_2F_3AsF_6$	35	-	(X)	-	X	-	No
21	$RbBrF_6$	21	-	-	-	-	-	Yes
22	$KClF_4$	21	-	-	-	-	-	Yes

TABLE 4. (continued)

Reactant No.	Reactant Composition	Ref.	F, (weight percent)	Cost	Physical Properties	Reactivity/ Safety	Availability	Acceptable
23	ClF_2BF_4	40	–	–	X	–	–	No
24	$ClF_3O \cdot BF_3$	41	–	–	–	–	–	Yes
25	$CsBrF_6$	21	–	–	–	–	–	Yes
26	XeF_2	37	–	(X)	(X)	–	(X)	Yes
27	$NCVF_6$	30	X	–	–	(X)	–	No
28	$XeF_2 \cdot MnF_4$	36,37	X	(X)	–	–	(X)	No
29	$XeF_2 \cdot VF_5$	38,39	X	(X)	–	(X)	(X)	No
30	MnF_4	31,32	X	–	(X)	–	–	No
31	$LiMnF_5$	31	X	–	–	–	–	No
32	$KMnF_5$	42,43	X	–	–	–	–	No

17

classification did not eliminate that reactant from consideration. The final column in table 4 depicts the state of acceptability which was used as the guideline in elimination of candidate reactants from further consideration.

After elimination of the candidates which were found unacceptable under any of the criteria, the remainder were compiled for rating according to the criteria discussed earlier. The rating for each criterion was from 0 to the maximum value of the weighting factor. Although the rating of each reactant or system within each of the criteria was subjective, the rating was derived by comparison with the other candidates. The summation of the ranking criterion values led to a score for each candidate and a subsequent ordering and identification of the most promising of the candidates.

The reactants, their ratings in the various areas, and their cumulative ratings are shown in table 5. The candidates are arranged in order of their cumulative ratings. Reactants currently under investigation were also included for comparison purposes. The reactants NF_4BF_4 and $LiMnF_5$ were considered marginal because of a low rating in the area of availability and cost for the former and fluorine content for the latter.

The fluorine content ratings were made based on a rating value-fluorine content correlation plot. This plot gave the highest rating of 25 to reactants having 40 weight percent fluorine or greater, and a rating of 0 for compounds having 15 weight percent fluorine or less. The cost factor was also derived from a rating value-cost correlation plot with the highest value (20) allotted to reactants with costs of \$30/lb or less in 10,000-lb lots. The other factors were defined more subjectively. The stability-safety criterion was based primarily on cumulative toxicity which downrated the antimony compounds and upon overall stability, a factor that influenced the low ratings for XeF_2 and $ClF_3O \cdot BF_3$.

The total ratings, based on a maximum value of 100, ranged from 28 to 79. With the uncertainties inherent in such ratings, the first seven reactants can be considered essentially equivalent in value.

18

TABLE 5. REACTANT RATING AND RANKING

Reactant Composition	Fluorine Content (25)	Availability, Cost (20)	Ranking Criteria Stability, Safety (35)	Product Contamination (15)	Ignition, Combustion (5)	Total Rating (100)
KBrF$_6$	20	19	25	10	5	79
KClF$_4$	15	20	25	10	5	75
NOBrF$_4$	18	20	20	10	3	71
RbBrF$_6$	14	17	25	10	5	71
CsBrF$_6$	10	17	25	10	5	67
(NO)$_2$MnF$_6$	10	17	20	12	5	64
NF$_4$SbF$_6$	14	16	15	8	5	58
ClF$_3$O·BF$_2$	11	12	12	10	3	48
NF$_3$O·SbF$_5$	4	9	15	8	3	39
XeF$_2$	7	2	6	8	5	28
NF$_4$BF$_4$	25	(1)	25	10	5	66
LiMnF$_5$	(1)	20	25	15	5	66

Theoretical Analysis of Reactant Systems

In addition to the theoretical equilibrium calculations performed for each reactant to determine the degree of dissociation at fixed temperature levels (which provided the input for table A-1 in appendix A), theoretical equilibrium calculations were also performed for reactant systems combining the candidate reactants with various fuels. These calculations yielded the theoretical flame temperature and combustion product composition as a function of formulation composition, thereby providing a convenient means of comparing the potential of the candidates. It must be recognized, of course, that these calculations are only as valid as the thermodynamic data available. For those candidates that reached this stage of evaluation, only those systems containing manganese suffered from a relatively high uncertainty owing to the lack of current data for manganese species. All others are covered by the JANNAF Thermochemical Data Tables.

The results of these calculations are summarized in table 6 which tabulates the weight percent fluorine available as F, F_2, or NF_3. The reactant candidates were all evaluated initially with two fuels, Si_3N_4 and Mg_3N_2. The fluorine yield from all reagents except $(NO)_2MnF_6$ was found to be equal to or greater than 10 percent by weight with either one or both fuels. This result led to the early elimination of $(NO)_2MnF_6$ as a viable candidate.

The question of the degree of degradation of fluorine yield as the result of the use of polytetrafluoroethylene as a combination fuel and binder led to the next series of calculations. Here it was found that all of the reactant candidates except $KClF_4$ and $LiMnF_5$ experienced considerable reduction in fluorine yield. $KClF_4$ and $LiMnF_5$, even with the reduction in yield, met or essentially met the goal of 10 percent fluorine by weight. In these instances, the fluorocarbon could be effectively used as a processing aid in the formulation of gas generator grains.

The effect of incomplete conversion in the preparation of reactants $KBrF_6$ and $KClF_4$ on the resultant fluorine yield was evaluated. This evaluation was made because early literature references showed incomplete conversions to the products with some unconverted KF present. However,

20

TABLE 6. MAXIMUM CALCULATED FLUORINE YIELD COMPOSITIONS

System No.	Reactant	Reactant Weight Percent	Fuel	Fuel Weight Percent	Flame Temperature, (K)	Weight Percent Fluorine (F, F_2, NF_3)
2311	$(NO)_2MnF_6$	93.00	Si_3N_4	7.00	1177	5.41
2314	$NOBrF_4$	90.00	Si_3N_4	10.00	1588	9.91
2316	$KBrF_6$	89.00	Si_3N_4	11.00	1629	10.50
2317	$KClF_4$	94.00	Si_3N_4	6.00	1126	13.67
2321	$LiMnF_5$	95.00	Si_3N_4	5.00	1395	3.34
2325	$(NO)_2MnF_6$	91.00	Mg_3N_2	9.00	1350	8.77
2324	$NOBrF_4$	88.00	Mg_3N_2	12.00	1700	12.76
2326	$KBrF_6$	88.00	Mg_3N_2	12.00	1605	13.51
2327	$KClF_4$	94.00	Mg_3N_2	6.00	1101	16.44
2372	$LiMnF_5$	99.00	Mg_3N_2	1.00	921	10.86
2344	$KMnF_5$	99.00	Mg_3N_2	1.00	483	8.82
2343	$KBrF_6-KF$ (95/5)	88.00	Mg_3N_2	12.00	1629	12.60
2342	$KClF_4-KF$ (95/5)	95.00	Mg_3N_2	5.00	980	15.42
2335	$(NO)_2MnF_6$	80.00	$(C_2F_4)_n$	20.00	1251	2.28
2018	$NOBrF_4$	75.00	$(C_2F_4)_n$	25.00	1622	3.80
2334	$KBrF_6$	75.00	$(C_2F_4)_n$	25.00	1521	4.51
2333	$KClF_4$	75.00	$(C_2F_4)_n$	25.00	1040	9.49
2336	$LiMnF_5$	99.00	$(C_2F_4)_n$	1.00	752	11.23
2349	$KClF_4$	88.00	NaN_3	12.00	877	16.62
2350	$LiMnF_5$	99.00	NaN_3	1.00	791	11.70
2354	$KClF_4$	95.00	AlN	5.00	1024	15.93
2355	$LiMnF_5$	99.00	AlN	1.00	930	10.60
2359	$KClF_4$	97.00	Al	3.00	1104	17.56
2361	$LiMnF_5$	99.00	Al	1.00	1079	9.87
2385	$LiMnF_5$	99.00	Mg	1.00	1030	10.42

current experience had led to the conclusion that conversions of 95 percent or higher could be expected under carefully conducted synthesis conditions. The theoretical calculations were therefore conducted with the appropriate level of KF contaminant. The calculated fluorine yield exhibited an almost linear dependence on contamination level in this range with approximately a 5 percent reduction in fluorine yield.

An alternative pentafluoromanganate salt, $KMnF_5$, was also evaluated with Mg_3N_2. As anticipated, the increase in formula weight resulting from the replacement of lithium by potassium reduced the fluorine yield proportionately. Consequently, this reactant was not considered further.

Both $LiMnF_5$ and $KClF_4$ were evaluated using NaN_3, AlN, and Al as common fuels. In all cases, the goal of 10 percent fluorine by weight was met or essentially met with considerably better yield derived from $KClF_4$. $LiMnF_5$ was evaluated with magnesium in addition and met the minimum goal requirement. The compositions giving the highest fluorine yield with $LiMnF_5$ in these instances fell in the very low fuel range, approximately 1 percent or lower.

The more complete summaries of the theoretical calculations from which table 6 was digested are collected in appendix B. These tables list, in addition to the parameters already specified, the concentrations of all products of any consequence, both condensed and gaseous.

Based on the foregoing analysis of candidate reactants and reactant systems, a series of five reactants were selected for experimental evaluation in the task 2 efforts. These compounds, listed in the order presented in task 2, are: $NOBrF_4$, $(NO)_2MnF_6$, $KBrF_6$, $KClF_4$, and $LiMnF_5$. With the exception of the last reactant, the other compounds met all criteria discussed previously based on information available at the time of selection. As discussed in the conclusion section of this report, the influence of contaminating species significantly altered the acceptability of these reactants.

22

$LiMnF_5$ was included as a candidate because it represented the only reactant that could provide essentially pure fluorine upon decomposition. This factor was deemed sufficiently important to permit relaxation of the available fluorine content restraint for this reactant.

TASK 2: CHARACTERIZATION AND TESTING OF SELECTED CANDIDATE REACTANT SYSTEMS

The objective of this task was to evaluate the stability, ignitability, combustion, and exhaust properties of the candidate reactant systems selected on the basis of the task 1 efforts.

The experimental work performed toward achieving this objective was conducted in five successive stages: (1) synthesis of the candidate reactant in quantities sufficient for subsequent evaluations; (2) testing and rating of a broad spectrum of reactant-fuel systems for exothermic reactivity at elevated temperatures; (3) evaluating the compatibility and sensitivity of the reactants with fuels selected to introduce the least possible amount of contaminating gas products; (4) performing small-scale atmospheric pressure ignition and combustion tests on the reactant-fuel systems; and (5) pressing gas generator grains and evaluating their combustion in a motor at elevated pressures to determine pressure-burning rate data and flame temperature, and to analyze the gaseous combustion products to establish the extent of generation of fluorine gas.

The experimental procedures used throughout task 2 investigations were essentially equivalent for each of the candidate reactants. Consequently, these procedures are described in the section which follows and the experimental results achieved using these various procedures are subsequently set forth individually for each of the five selected reactants.

Experimental Procedures

All of the fluorine compounds used for synthesis of the reactants and most of the fuels employed in this program were obtained from two sources, Ozark-Mahoning Company and Alfa-Ventron Company. The chemicals were used as-received and opened only in the dry box or to a vacuum system.

All fluorine reactant syntheses were conducted employing the all-metal vacuum system illustrated in figure 1. Two nickel reactors of 150-ml capacity and one stainless steel reactor of 60-ml capacity were used for the synthesis work. The specific synthesis procedures employed for each reactant synthesized are described in the sections devoted to the results obtained with the reactants.

Wet chemical analyses on fluorine-containing oxidizers were made in part by Galbraith Laboratories, Inc. of Knoxvile, Tenn. X-ray (Debye-Sherrer powder pattern) analyses were made by Analex of Palo Alto, CA., and nuclear activation analyses were made by General Activation Analysis, Inc. of San Diego, CA. Mass spectrographic analysis on gas products was made by Ultrachem Corporation of Walnut Creek, CA.

Since all of the fluorinated reactants and some of the fuels employed in this program were sensitive to decomposition by moisture to some degree, they were handled entirely in an inert atmosphere of dry nitrogen. A "Dri-Lab" inert atmosphere chamber, manufactured by D. L. Herring Corporation, was employed for practically all transfer operations.

Differential thermal analysis tests (DTA) were made using 10- to 15-mg samples of the dry gas generator mixtures under a nitrogen atmosphere in a 0.9-in.-diameter by 1.5-in.-long aluminum block heated by an 80-watt ITT Vulcan heating probe which produced a heating rate of 30 to 40 C/min. The absolute values and differential temperatures were recorded using a two-pen strip chart recorder. From analysis of the charts, the relative values of the autoignition temperatures and the magnitude of the associated exothermic energies were determined. In addition, the presence of endothermic melting occurring before attaining the autoignition temperature could be detected. Due to the reactive nature of the fluorinated reactants employed, the samples were tested in both glass and stainless steel sample tubes to eliminate any possible oxidizer-glass exotherms.

24
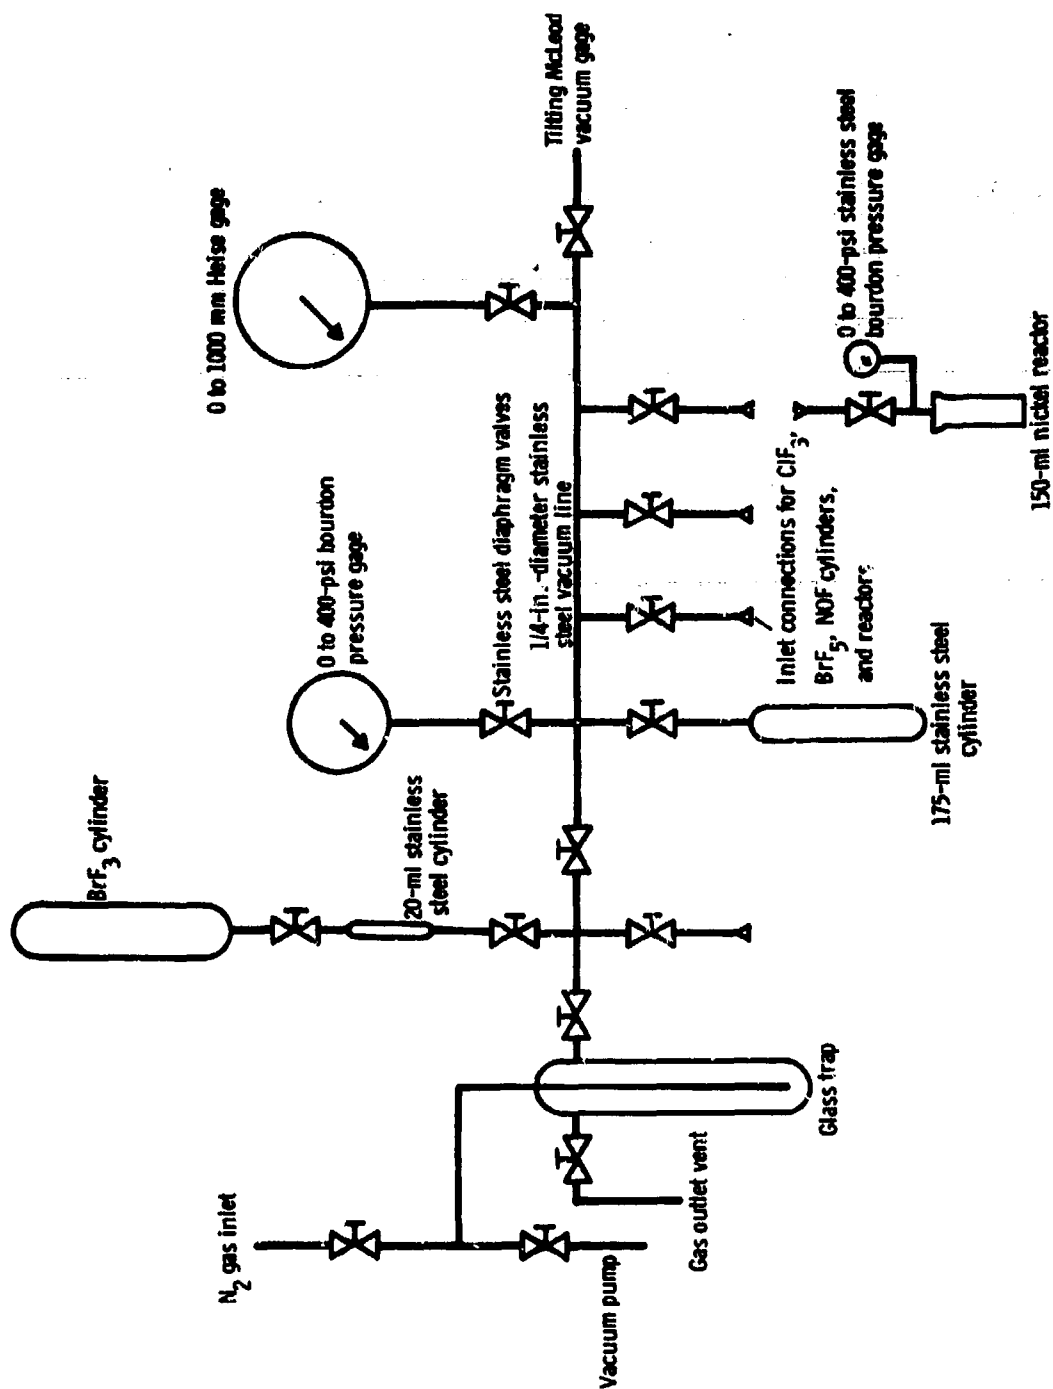
Figure 1.   All-Metal Vacuum System

25

A large number of reactant systems was screened with atmospheric
pressure combustion studies. The nitrogen atmosphere ignition and combustion
testing apparatus used is shown in figure 2. It is essentially an all-glass
system to allow for visual observations of the ignition and burning
processes. A stainless steel grain case was used only in cases where flame
temperatures and atmospheric burning rates were being measured.
Chromel-alumel thermocouples attached to a 5-124 CEC recording oscillograph
were used to obtain flame temperatures and burning rates.

Impact and friction sensitivity tests were made on all reactant-fuel
systems considered promising from the ignitability and combustion testing.
The impact tests were conducted with an Olin-Mathieson-type drop weight
tester. The samples employed in these tests were placed in sealed sample
holders in a nitrogen atmosphere dry box to avoid hydrolytic reaction before
or during the tests. The friction tests were conducted using an ESSO
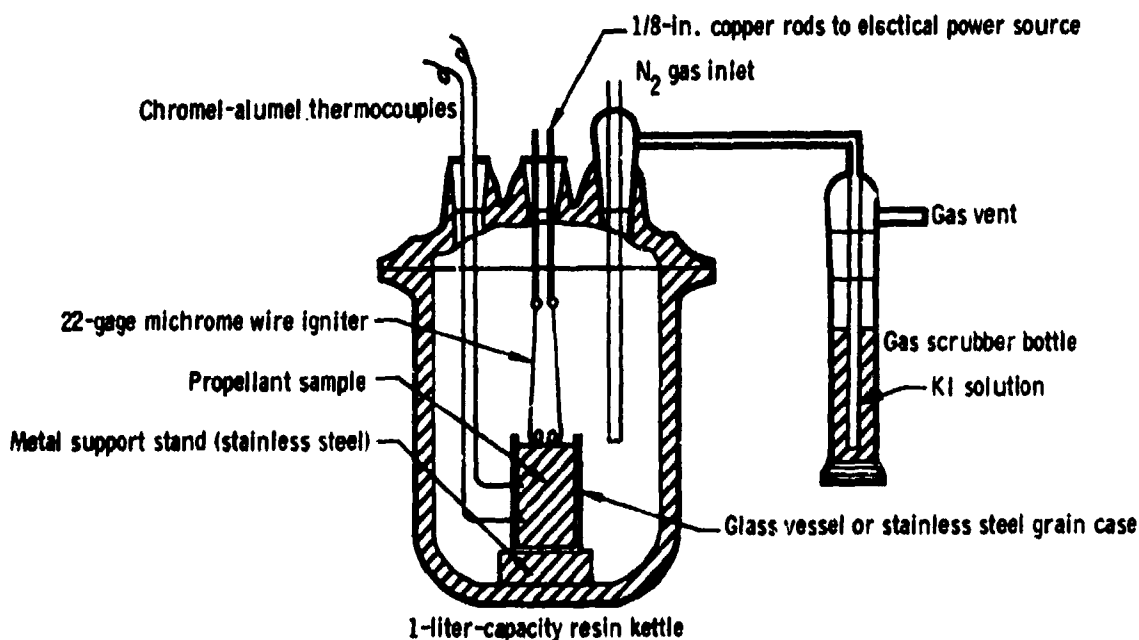
Figure 2. Ignition and Combustion Testing Apparatus

26

friction tester. The tester was placed in a large plastic bag and flushed with nitrogen until the relative humidity was below 10 percent before starting testing. The samples were mixed with diamond grit and a maximum of 70 ft-lb of work applied.

The most promising reactant system candidates for fluorine gas generators were selected for small motor testing based on the atmospheric ignition and combustion screening tests described above. The formulations were mixed and fabricated into grains for test firing in a small test motor. The grain cases were constructed of stainless steel tubing 1.92 in. long having an internal diameter of 0.9 in. Four pressings of equal amounts of the thoroughly mixed dry reactant-fuel composition were made per grain. A force of 2000 lb (3000 psi) was applied with each pressing using a stainless steel punch and an RC-55 Enerpac 5-ton hydraulic cylinder. The entire operation was conducted in a dry box under constant nitrogen flush. The small test motor assembly is shown in figures 3 and 4. The material of construction was stainless steel with Teflon O-ring seals. The assembly consisted of tie rods, transducer and thermocouple attachment tee, solid spacer, grain case, end closures (with a nichrome wire igniter sealed through one end closure), motor body, and steel nozzle and holder attachment. The pressures developed in the motor were determined with a 0- to 1000-psia-range Statham transducer, to which was attached a 1000-psig rupture disc assembly. The transducer was attached to a 5-124 CEC recording oscillograph operated at a chart speed of .25 in./sec. The chamber pressure was varied from 14.7 to 500 psia by variations in the nozzle diameter. The exhaust line from the motor was provided with gas sampling takeoff and vacuum.

Experimental Results

For the task 2 evaluation, the five reactants selected from the task 1 studies were (1) nitrosonium tetrafluorobromate, $NOBrF_4$; (2) nitrosonium hexafluoromanganate, $(NO)_2MnF_6$; (3) potassium hexafluorobromate, $KBrF_6$; (4) potassium tetrafluorochlorate, $KClF_4$; and (5) lithium pentafluoromanganate, $LiMnF_5$. The synthesis, DTA, ignition and combustion studies, hazard evaluation, and small motor test results are consolidated for each reactant in the subsections which follow.

27
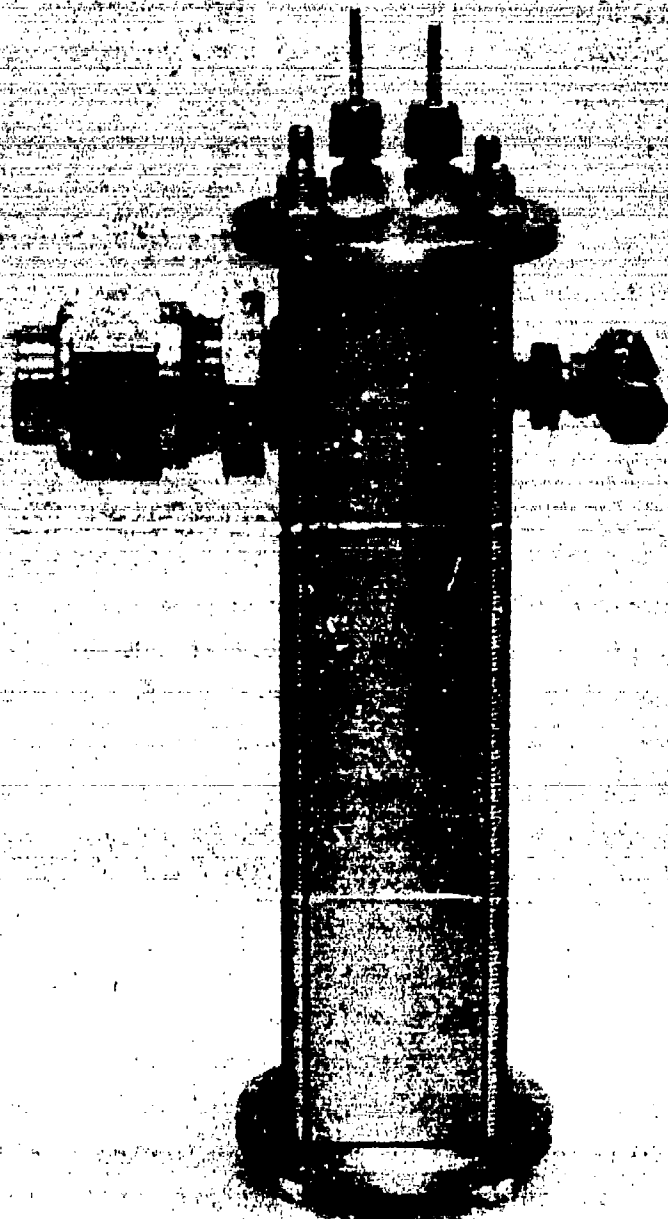
Figure 3. Small Test Motor
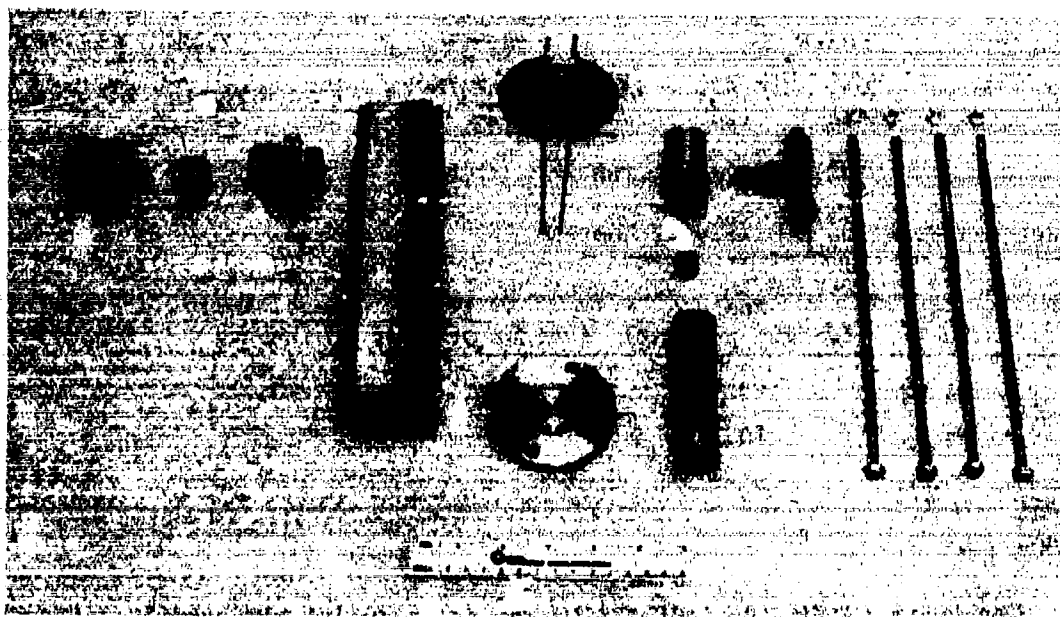
Figure 4. Small Test Motor - Exploded View

Nitrosonium Tetrafluorobromate - The compound NOBrF$_4$ is well-characterized
and exhibits adequate stability as a reactant for a fluorine gas generator.
The reactant is easily synthesized pure by condensation of NOF with BrF$_3$[24],
both of these precursors being readily available. For this program, this
synthesis method was employed. Bromine trifluoride was placed in a nickel
reactor by a vacuum-gravity technique and a slight stoichiometric excess of
NOF was added by vacuum distillation. A total of 32.3 g of NOBrF$_4$ was
prepared with a 96.6 percent conversion as shown in table 7. DTA tests
showed that NOBrF$_4$ decomposed at 180 C with a large endothermic heat of
dissociation.

During preparation of candidate reactant systems for DTA tests,
spontaneous ignition occurred upon mixing NOBrF$_4$ with B, Si$_3$N$_4$, S, or BN. On
the other hand, tetrafluoroethylene, Mg$_3$N$_2$, Kel-F, Al, Mg, and NaN$_3$ were
suitably compatible to permit mixing and DTA results were obtained as shown
in table 8. The NaN$_3$/NOBrF$_4$ composition gave an exothermic reaction at
102 C, which is considered marginal for a safe gas generator system.

TABLE 7. PREPARATION AND PROPERTIES OF NOBrF₄ REACTANT SYSTEMS

Preparation of NOBrF₄

Prep. No.	NOF, (g)	NOF, (moles)	BrF₃, (g)	BrF₃, (moles)	BrF₃/NOF, (mole ratio)	Reaction Temp. (C)	Conversion, (percent)
1	8.986	.183	24.667	.180	.984	20	96.6

Impact and Friction Sensitivity Tests of NOBrF₄ and Mg₃N₂

Test No.	Fuel	Fuel, (weight percent)	NOBrF₄, (weight percent)	Impact Sensitivity, (kg-cm)	Friction Sensitivity[a]
1	Mg₃N₂	13.5	86.5	7.6	-
2	Mg₃N₂	10.1	89.9	-	no sensitivity

[a] Diamond grit at 70 ft-lb.

The NOBrF₄/Mg₃N₂ reactant system was selected for atmospheric pressure ignition-combustion testing. Ignition was observed to occur readily with an 87 weight percent NOBrF₄ composition, combustion was complete, and the burning rate was moderate in a tamped powder configuration. Impact and friction tests were made on this composition; the mixture was found to be very impact-sensitive but not friction-sensitive, as shown in table 7.

Work on NOBrF₄ was not continued in light of the potential detrimental effects of BrF and NOF on deactivation and the high reactivity of NOBrF₄ with fuels observed during the early exploratory tests described above.

Nitrosonium Hexafluoromanganate - The compound $(NO)_2MnF_6$ has been reported to have sufficient stability to be considered as a reactant for fluorine gas generation. For preliminary screening studies, the compound was synthesized by the procedure of Bouy[20] by reaction of MnF₃ and NOF in a large excess of BrF₃ at 100 C. The excess BrF₃ was subsequently removed at 120 to 150 C. The conversion, noted as slightly greater than 100 percent, was probably a result of the presence of NOBrF₄ produced from a slight stoichiometric excess of NOF introduced into the reactor. DTA of the $(NO)_2MnF_6$ reaction product

TABLE 8. DTA OF $NOBrF_4$ AND VARIOUS FUELS

Test No.	Fuel	Fuel Weight Percent	$NOBrF_4$, (weight percent)	Endotherms, (C)	Exotherms, (C)
1	None	-	100	179s	
2	$(C_2F_4)n$	9.9	90.1	190s	
3	B	-	-	Spontaneous ignition on mixing	
4	Si_3N_4	10.7	89.3	200m Sporadic ignition on mixing	83s
5	Mg_3N_2	24.5	75.5	176s	
6	Kel-F	10.6	89.4	179s	
7	S	-	-	Spontaneous ignition on mixing	
8	Al	10.1	89.9	179s	
9	Mg	10.6	89.4	171s	
10	NaN_3	10.6	89.4	157m-w	102s
11	BN	-	-	Gas evolution on mixing	

NOTE: s = strong, m = medium, w = weak

showed no tendency for decomposition below 200 C (see table 9). These data thereby confirm the reported stability of the compound.

Mixtures of $(NO)_2MnF_6$ and selected fuels were made to provide preliminary DTA data. As shown in table 9, the material was found to be compatible with every fuel tested, including fuels that resulted in spontaneous ignition with $NOBrF_4$. DTA results showed most fuels with $(NO)_2MnF_6$ gave only endotherms at temperatures of 200 C or below (e.g.,

TABLE 9. DTA OF $(NO)_2MnF_6$ AND VARIOUS FUELS

Test No.	Fuel	Fuel Weight Percent	$(NO)_2MnF_6$, (weight percent)	Endotherms, (C)	Exotherms, (C)
1	None	-	100.0	200vw, 303w	290vw
2	$(C_2F_4)n$	9.0	91.0	200w, 300wm	284w
3	Al	8.8	91.2	200w, 300wm	254w, 287w
4	B	9.7	90.3	-	97wm, 138vs
5	Mg	10.5	89.5	200w, 298m	287w
6	S	10.1	89.9	195w, 271m	-
7	NaN_3	11.2	88.8	-	127s
8	Mg_3N_2	9.8	90.2	200w, 300m	287vw

NOTE: vs = very strong, s = strong, m = moderate, w = weak,
vw = very weak

perfluoroethylene, aluminum, sulfur, and magnesium nitride). Exotherms at
comparatively low temperatures were observed with boron (100 C) and NaN_3
(127 C); magnesium showed a higher exotherm at 287 C.

Because of the reduced fluorine levels calculated for reactant systems
employing $(NO)_2MnF_6$, no further work was conducted with $(NO)_2MnF_6$.

Potassium Hexafluorobromate - The compound $KBrF_6$ has previously been shown to
be a thermally stable material exhibiting high reactivity characteristics
with fuels.

For this work, $KBrF_6$ was prepared from KF and BrF_5 according to the
procedure described by MacLaren et al.[21] An excess of BrF_5 was vacuum
distilled onto KF in a nickel reactor and this mixture was heated to 100 C
for several hours. The unreacted BrF_5 was subsequently removed by vacuum

distillation. Five preparations of $KBrF_6$ were made as shown in table 10. As previously reported, it was found that the conversion to $KBrF_6$ was about 80 percent and independent of the reaction time and amount of excess BrF_5. To improve the conversion of KF to $KBrF_6$, the reaction product from preparation 5 was removed from the reactor, pulverized, and returned to the reactor with additional BrF_5. The conversion increased from the 80 percent level to approximately 95 percent by this treatment.

$KBrF_6$ is thermally stable to about 200 C as shown by the DTA results in table 11. With fuels, however, the compound was found to react at much lower temperatures. As with $NOBrF_4$, $KBrF_6$ reacted spontaneously when mixed with boron. With Si_3N_4 and SiO_2, exotherms were measured at temperatures of 130 to 160 C. No exotherms to the maximum experimental temperature of 500 C were observed with perfluoroethylene or Mg_3N_2.

Impact and friction tests were made on a 92 weight percent $KBrF_6$/8 weight percent Mg_3N_2 composition and the impact sensitivity was measured to be 15 kg-cm with no measurable friction sensitivity. These results indicate that $KBrF_6$ systems are safer to handle than the equivalent $NOBrF_4$ systems.

An atmospheric pressure ignition and combustion test was conducted with a tamped mixture of 89.6 weight percent $KBrF_6$ and 10.4 weight percent Mg_3N_2. Ignition occurred readily, and the composition burned completely with a low burning rate.

A total of five grains of between 16 and 24 g each with the approximate composition of 90 weight percent $KBrF_6$/10 weight percent Mg_3N_2 were prepared by pressing at a nominal pressure of 3000 psi giving an average grain density of 2.21 g/cc. The test data obtained from these grains are summarized in table 12. One grain was fired in the atmospheric pressure test apparatus and the other four were tested in the small test motor. The flame temperature measured by a thermocouple in the test grain at 1 atm varied from 1143 to 1403 K. Plugging of the motor nozzle with melted and resolidified igniter wire particles was a problem in two of the tests. This problem was overcome by employing an oversized nozzle and maintaining a constant nitrogen flow to

33

TABLE 10. PREPARATION OF $KBrF_6$

Prep. No.	KF, (g)	KF, (moles)	BrF_5, (g)	BrF_5, (moles)	BrF_5/KF, (mole ratio)	Reaction Temp., (C)	Conversion, (percent)
1	4.832	.0832	20.55	.117	1.41	100	71.5
2	20.945	.360	105.7	.604	1.68	135	84.5
3	19.460	.335	105.4	.603	1.80	135	82.1
4	28.088	.483	101.4	.580	1.20	135	81.5
5	25.297	.435	103.6	.592	1.36	135	79.4
6	a	(75.710g)	58.7	.336	-	135	94.5

[a] Product from reaction No. 5.

TABLE 11. DTA OF $KBrF_6$ AND VARIOUS FUELS

Test No.	Fuel	Fuel Weight Percent	$KBrF_6$, (weight percent)	Endotherms, (C)	Exotherms, (C)
1	-	-	100	190w, 292w	-
2	$(C_2F_4)n$	9.5	90.5	190w, 292w	-
3	B	-	-	Spontaneous ignition on mixing	
4	Si_3N_4	9.6	90.4	-	130 vs (flame)
5	Mg_3N_2	12.5	87.5	184vw, 279vw	-
6	SiO_2	10.3	89.7	-	161m
7	Si_3N_4	5.0	95.0	-	135s
8	Si_3N_4	1.0	99.0	186vw, 287vs	-

NOTE: vs = very strong, s = strong, m = medium, w = weak, vw = very weak

TABLE 12. GRAIN COMBUSTION TESTS OF $KBrF_6$ AND Mg_3N_2

Test No.	Fuel	Fuel Weight Percent	$KBrF_6$, (weight percent)	Grain Weight, (g)	Grain Length, (in.)	Grain Density, (g/cc)	Burning Rate, (in./sec)
1	Mg_3N_2	10.2	89.8	16.637	.74	2.16	.03

Test pressure: 14.7 psia - combustion complete - some liquefaction during combustion

| 2 | Mg_2N_3 | 9.5 | 90.5 | 22.467 | .99 | 2.19 | - |

Combustion complete - no pressure measurement- residue: 64.6%

| 3 | Mg_3N_2 | 10.0 | 90.0 | 21.967 | .95 | 2.23 | - |

Ignition spike - 1000-psi rupture disk relieved

| 4 | Mg_3N_2 | 9.6 | 90.4 | 23.737 | 1.02 | 2.24 | - |

Melted ignition wire plugged nozzle - 1000-psi rupture disk relieved

| 5 | Mg_3N_2 | 10.4 | 89.6 | 23.694 | 1.01 | 2.25 | .05 |

Nitrogen flow permitted use of oversize nozzle - N_2 pressure: 63-psia- F_2 pressure: 127-psia max.

provide a pressure level in the motor before and during combustion. Measured burning rates were comparatively low, .03 in./sec at 14.7 psia and .05 in./sec at approximately 100 psia.

From these tests, it appeared that this solid reactant system could be successfully developed. However, efforts on the $KBrF_6$ system were discontinued during the task 2 portion of the program because of the uncertainties of the influence of the combustion product, BrF, on laser performance.

Potassium Tetrafluorochlorate - The preparation and identification of $KClF_4$ has been reported; however, information on the physical and chemical properties of this compound is limited.

For the investigations in this program, $KClF_4$ was prepared from KF and

ClF_3 according to the procedure described by MacLaren et al.[21] A series of eight syntheses was conducted to prepare sufficient material for test evaluation. The experimental conditions are given in table 13. A total of 547 g was prepared with purities ranging from 92.8 to 98.5 percent. The lowest conversion was obtained in preparation No. 2, whereby a stoichiometric quantity of ClF_3 was added to the KF. In all other preparations, excess ClF_3 was used and subsequently removed by vacuum distillation.

DTA tests of $KClF_4$ showed some endothermic activity at 97 to 100 C which is most likely melting. The higher endotherms at 230 to 240 C are consistent with the decomposition temperature reported in the literature.

An extensive number of fuels with $KClF_4$ were examined by DTA, as shown in table 14. With boron, Li_3N, and Ca_3N_2, ignition between $KClF_4$ and the fuels occurred on mixing. Low temperature exotherms were observed with sulfur, BN, and NaN_3. Of the nitrides, only Mg_3N_2 showed stability above 200 C. Compared to the previous reactants, the reactivity of $KClF_4$ appeared less than either $NOBrF_4$ or $KBrF_6$.

An atmospheric pressure ignition and combustion test was made with an 88.5 weight percent $KClF_4$/11.5 weight percent Mg_3N_2 mixture. Incomplete combustion was obtained with the tamped powder which might be expected from the weak exothermic reactivity recorded by DTA. On the other hand, a tamped mixture of 89.9 weight percent $KClF_4$/10.1 weight percent NaN_3 ignited easily, had a reasonable burning rate, and burned completely.

The impact and friction sensitivities of $KClF_4$ with the most promising fuels were evaluated and the results are listed in table 15. The candidate $KClF_4$ reactant systems are all safe to handle according to these results if the proper precautions are taken. The impact sensitivities for the reactants appear to correlate with their reactivity with the fuels in that the impact sensitivities decrease in the order: $NOBrF_6 > KBrF_6 > KClF_4$.

A total of 16 pressed grains were prepared from various compositions of $KClF_4$ and fuels using a compaction pressure of 3000 psi. One grain, prepared

36

TABLE 13. PREPARATION OF $KClF_4$

Prep. No.	KF, (g)	KF, (moles)	ClF_3, (g)	ClF_3, (moles)	ClF_3/KF, (mole ratio)	Reaction Temp., (C)	Conversion, (percent)
1	9.199	.158	33.9	.367	2.32	130	97.7
2	16.945	.292	27.0	.292	1.00	135	92.8
3	21.921	.377	49.5	.535	1.42	135	96.4
4	23.634	.407	48.4	.523	1.29	135	96.7
5	27.056		111.8	1.209	2.59	135	97.1
6	26.477	.456	98.1	1.061	2.33	135	94.0
7	28.372	.488	84.3	.912	1.87	135	97.4
8	24.806	.427	94.4	1.021	2.39	135	98.5

using Mg_3N_2 as the fuel, was tested at atmospheric pressure and did not sustain combustion. All other grains were tested in the small test motor. Five $KClF_4$-NaN_3 grains were prepared; however, during the preparation of three other $KClF_4$-NaN_3 grains, spontaneous ignitions occurred during either the mixing or pressing operations. All five $KClF_4$-NaN_3 grains fired in the motor ignited and burned successfully. Test data are noted in table 16 as tests 3 through 7. Burning rates varied from .05 to .09 in./sec. The $KClF_4$-NaN_3 grain used in test No. 8 was fired into an evacuated holding cylinder for gas sampling. The burning rate was very low and the limited quantity of gas evolved in comparison to the other tests showed the influence of a large pressure effect. A sample of the combustion products was submitted for mass spectrometer analysis; however, instrumental difficulties prevented a satisfactory analysis.

A total of seven additional grains were prepared from the $KClF_4$-Al reactant system using aluminum powder of 6 to 9 microns. The first grain had a 95 weight percent $KClF_4$/5 weight percent Al composition and was successfully fired in the motor (test No. 10). The burning rate at a chamber

TABLE 14. DTA OF $KClF_4$ AND VARIOUS FUELS

Test No.	Fuel	Fuel Weight Percent	$KClF_4$, (weight percent)	Endotherms, (C)	Exotherms, (C)
1	-	-	100.0	100w, 236w, 265w	-
2	$(C_2F_4)n$	10.1	89.9	100w, 233w, 260w	-
3	Si_3N_4	9.6	90.4	97w	149vs
4	BN	16.8	83.2	-	100w, 119s
5	B	-	-	Spontaneous ignition on mixing	
6	Mg_3N_2	22.2	77.8	97w, 239w, 260w	285w
7	Al	10.0	90.0	97w	281s
8	Mg	9.9	90.1	97w, 238w, 265w	260w
9	S	9.7	90.3	-	94vs
10	NaN_3	10.1	89.9	-	105s
11	Kel-F	10.3	89.7	97w, 233w, 287w	300w
12	Li_3N	-	-	Spontaneous ignition on mixing	
13	Ca_3N_2	-	-	Spontaneous ignition on mixing	
14	AlN	5.1	94.9	101w, 240w, 289w	168m

NOTE: vs = very strong, s = strong, m = medium, w = weak

pressure of approximately 300 psia was .04 in./sec. The high theoretical
flame temperature of 1700 C and the presence of corrosive gases combined to
cause partial consumption of the stainless steel grain case. Five attempts
were made to successfully burn grains prepared with a lower aluminum content
of 97 weight percent $KClF_4$/3 weight percent Al. The first grain could not be
ignited even after prolonged heating with a nichrome wire grid. To
facilitate ignition, more easily ignited compositions were placed as a cap on
top of the 97 weight percent $KClF_4$/3 weight percent Al grains. The first cap

TABLE 15. SENSITIVITY TEST DATA OF KClF$_4$ AND VARIOUS FUELS

Test No.	Fuel	Fuel Weight Percent	KClF$_4$, (weight percent)	Friction Sensitivity, (kg-cm)	Friction Sensitivity[a]
1	Mg$_3$N$_2$	11.5	88.5	36.5	-
2	Mg$_3$N$_2$	10.1	89.9	-	No sensitivity
3	NaN$_3$	10.1	89.9	16.0	No sensitivity
4	Al	5.4	94.6	54.0	No sensitivity
5	AlN	5.1	94.9	13.3	No sensitivity

[a] Diamond grit at 70 ft-lb.

employed was a 90 weight percent KBrF$_6$/10 weight percent Mg$_3$N$_2$ composition; this cap ignited satisfactorily but ignition of the grain did not occur (test No. 12). A cap of 95 weight percent KClF$_4$/5 weight percent Al was next examined and gave the same results. The cap residue was removed from the grain and a second cap of 90 weight percent KClF$_4$/10 weight percent NaN$_3$ successfully ignited the grain (test No. 13). This same composition cap was not successful in igniting a second grain (test No. 14), nor was a cap comprised of AgF$_2$-Mg.

A grain was formulated with 96 weight percent KClF$_4$, 3 weight percent Al, and 1 weight percent NaN$_3$. While it could not be ignited directly with the hot nichrome igniter grid, combustion was complete when capped with an 89 weight percent KClF$_4$/11 weight percent NaN$_3$ composition. A burning rate of .03 in./sec was measured at a chamber pressure of 30 to 80 psia.

Four grains were pressed and fired in the small motor with a 95 weight percent KClF$_4$/5 weight percent AlN composition. They all ignited easily and burned completely with burning rates ranging from .014 to .055 in./sec. One grain was fired into a holding cylinder, previously passivated with fluorine, which had been evacuated and filled to one atmosphere with helium. A sample of the combustion gas products was submitted for mass spectrographic

TABLE 16. COMBUSTION OF GRAINS OF KClF$_4$ AND VARIOUS FUELS

Test No.	Fuel	Fuel Weight Percent	KClF$_4$, (weight percent)	Grain Weight (g)	Grain Length (in.)	Density (g/cc)	Burning Rate (in./sec)	Chamber Pressure (psia)	Residue Weight (percent)
1	Mg$_3$N$_2$	6.2	93.8	9.93	.57	1.67	-	-	-
	Ignition and combustion occurred only in vicinity of igniter								
2	NaN$_3$	11.0	89.0	-	-	-	-	-	-
	Ignited on mixing								
3	NaN$_3$	11.0	89.0	17.46	.99	1.69	.05	60[a]	58.8
4	NaN$_3$	11.0	89.0	17.74	1.01	1.68	.05	80[a]	67.0
5	NaN$_3$	11.0	89.0	19.43	1.11	1.67	-	-	-
	Spontaneous ignition of grain during motor loading operation								
6	NaN$_3$	11.0	89.0	19.32	1.09	1.69	.09	40	55.0
7	NaN$_3$	11.0	89.0	18.05	1.03	1.68	.05	35	55.1
8	NaN$_3$	11.0	89.0	19.42	1.10	1.69	-	500mm	68.3
	Vacuum ignition, products collected for analysis								
9	NaN$_3$	11.0	89.0	-	-	-	-	-	-
	Ignited on mixing								
10	Al	5.0	95.0	18.56	1.01	1.76	.04	~300	-
	Nozzle plugging occurred, grain case wall burned								
11	Al	3.0	97.0	18.83	1.01	1.79	-	-	-
	Grain did not ignite								

TABLE 16 (continued)

Test No.	Fuel	Fuel Weight Percent	KClF$_4$, (weight percent)	Grain weight, (g)	Grain Length, (in.)	Density, (g/cc)	Burning Rate, (in./sec)	Chamber Pressure, (psia)	Residue Weight, (percent)
12	Al	3.0	97.0	18.91	1.03	1.76	-	-	-
	Igniter cap of 89.7 weight percent KBrF$_6$/10.3 weight percent Mg$_3$N$_2$ did not ignite grain								
13	Al	3.0	97.0	19.29	1.05	1.77	.05	~50	-
	Igniter cap of 95.0 weight percent KClF$_4$/5.0 weight percent Al did not ignite grain								
	Igniter cap of 90.0 weight percent KClF$_4$/10.0 weight percent NaN$_3$ ignited grain, successful combustion								
14	Al	3.0	97.0	20.15	1.08	1.77	-	-	-
	Two separate igniter caps (90.0 weight percent KClF$_4$/10 weight percent NaN$_3$, 95.0 weight percent AgF$_2$/5.0 weight percent Mg) failed to ignite grain								
15	Al NaN$_3$	3.0 1.0	96.0	16.32	.89	1.76	.03	~50	-
	Igniter cap of 88.9 weight percent KClF$_4$/11.1 weight percent NaN$_3$ required for ignition and combustion								
16	AlN	5.6	94.4	17.46	.94	1.78	.03	~400	81.1
	Screen filters plugged								
17	AlN	4.9	95.1	20.65	1.13	1.76	.014	50	48.4
	Combustion complete with intermittent burning								
18	AlN	5.0	95.0	20.66	1.13	1.76	.055	200	64.7
19	AlN	5.0	95.0	19.49	1.07	1.75	.024	~15	52.8
	Gas products collected for analysis								

a Nitrogen flow added to permit use of larger nozzles.

analysis. The analysis showed the major components of the sample to be ClF and Cl_2 accounting for over 90% of the sample. Minor components included CH_2ClF, CH_2F_2, CHF_3, and F_2. The $KClF_4$-AlN reactant system operated most successfully of the $KClF_4$ reactant systems.

Lithium Pentafluoromanganate - Very limited information was available from the literature on $LiMnF_5$. Hoppe, Dähne and Klemm[31] have reported preparing the compound by fluorinating $LiMnF_3$ at 450 to 500 C in a flow system with sublimation of $LiMnF_5$ and collection on a cold finger. Since this method is not considered practical for large-scale production, studies were performed under the IR&D program to define a more straightforward synthesis route to $LiMnF_5$. These studies applied the method for preparation of $KMnF_5$ of Sharpe and Woolf[30] to $LiMnF_5$.

A series of reactions was performed using variously MnF_3, MnO_2, or $MnCl_2$ as the starting material with LiF and BrF_3. A large excess of BrF_3, which acts both as a solvent and reactant, was used. From these experiments, it was determined that the reaction with $MnCl_2$ occurred readily at ambient temperature and the accompanying exotherm resulted in a significant temperature rise. Ten syntheses using $MnCl_2$ were conducted and are summarized in table 17. In each case, there was a pressure increase during reaction; percent conversion to $LiMnF_5$ on a weight basis was 95 to 100 percent. The gaseous products formed during the synthesis of $LiMnF_5$ (preparation No. 8), as analysed by mass spectrometer, are shown in table 18.

The Cl_2, BrCl, and Br_2 are expected products. The source of the hydrogen is not known. The $MnCl_2$, used as a starting material, was investigated to ensure that it was not a hydrate. Chlorine by analysis was 54.73 percent (theoretical = 56.35 percent) and, upon vacuum drying at 155 C, only a 1.27 percent weight loss was found. A sample was also submitted for X-ray analysis and found to match the ASTM d-spacings for anhydrous $MnCl_2$. It was concluded that the hydrogen was obtained from secondary reactions during the mass spectrometer analysis.

42

TABLE 17. PREPARATION OF LiMnF$_5$ AND MnF$_4$

Prep. No.	Mn Compound Halide	Mn Compound Halide, (moles)	LiF, (moles)	BrF$_3$, (moles)	BrF$_3$/Mn, (mole ratio)	Reaction Temperature, (C)	Conversion, (percent)	Remarks
1	MnCl$_2$	.0400	.403	.367	9.2	100	93.2	Rust solids
2	MnCl$_2$	.0719	.0729	.213	3.0	100	99.0	Gold solids
3	MnCl$_2$	.149	.148	.524	3.5	100	(100.0)	Gold solids
4	MnCl$_2$	.0899	.906	.330	3.7	100	94.9	Gold solids
5	MnCl$_2$	.101	.102	.455	4.5	100	93.8	Gold solids
6	MnCl$_2$	.0997	.0976	.348	3.5	100	97.5	Gold solids
7	MnCl$_2$	.2205	.2182	.5558	2.5	100	(102.3)	Gold solids
8	MnCl$_2$	.153	.166	.602	3.7	135	97.1	Gold solids
9	MnCl$_2$	.0588	.0614	.332	4.6	100	85.4	Rust solids
10	MnCl$_2$	.164	.167	.723	4.4	110	97.0	Gold solids
11	MnBr$_2$	.0637	.0665	.351	5.5	20	(100.1)	Greenish-gold solids
12	MnBr$_2$	.1358	.1379	.666	4.9	20	97.3	Greenish-gold solids
13	MnBr$_2$	.1393	.1384	.7194	5.2	20	92.9	Greenish-gold and rose-red solids

TABLE 17. (continued)

Prep. No.	Mn Compound Halide	Mn Compound Halide, (moles)	LiF, (moles)	BrF$_3$, (moles)	BrF$_3$/Mn. (mole ratio)	Reaction Temperature, (C)	Conversion, (percent)	Remarks
14	MnCl$_2$	.028	–	.35	12.7	110	MnF$_4$ (113.2)	Purplish–blue solids
15	MnBr$_2$	.0885	–	.3496	3.95	20	MnF$_4$ 96.2	Purplish–blue solids
16	MnF2	.08998	–	.5263	5.85	130	MnF$_4$ 96.8	Gray–blue solids

44

TABLE 18. LiMnF$_5$ SYNTHESIS PRODUCT GAS COMPOSITION

Compound	Mole Percent
Cl$_2$	60
BrCl	17
HCl	11
Br$_2$	9
HBr	2

The color of the products obtained from the LiF-MnCl$_2$-BrF$_3$ reactions has not always been consistent, as noted in table 17. As a result, samples were submitted to determine d-spacings from their X-ray powder patterns. The d-spacings show similarities (as compiled in appendix C) but do not match exactly. The ASTM index does not contain a pattern or d-spacings for LiMnF$_5$. None of the patterns indicate the presence of LiF, MnCl$_2$, MnF$_2$, or MnF$_3$.

Three preparations were made using MnBr$_2$ as a reactant. As in the case of MnCl$_2$, it was found on the basis of weight change that the reaction product is LiMnF$_5$ with conversions of 94 to 99 percent. With MnBr$_2$, the heat of reaction was greater than with MnCl$_2$, but the gaseous product pressure buildup was less, due to the liberation of Br$_2$ instead of Cl$_2$ which has lower vapor pressure at ambient temperature.

Three reactions to prepare MnF$_4$ were made using only manganese halides and BrF$_3$ to obtain a better understanding of the LiF-MnCl$_2$-BrF$_3$ and LiF-MnBr$_2$-BrF$_3$ reactions. The divalent halides MnF$_2$, MnCl$_2$, and MnBr$_2$ were employed. The reaction product in each case was purplish-blue to gray-blue, consistent with the literature. The solid reaction products from the fluoride and bromide reactions corresponded to MnF$_4$ on a weight basis with conversions of 96 and 97 percent, respectively. However, the chloride reaction product calculated 112.3 percent conversion on the basis of MnF$_4$ and a more reasonable 101.7 percent if MnF$_5$ is assumed the product. In each case, the product appeared to be stable at ambient temperature.

The results of wet chemical analyses of the various reaction products, $LiMnF_5$ and MnF_4, have not been completely satisfactory. In no case has analysis accounted for 100 percent of the sample, the missing constituents amounting to from 10 to 25 percent of each of six samples. The possibility of incomplete conversion of $MnCl_2$ (or $MnBr_2$) was evaluated by analysis for chlorine and bromine but together these elements account for less than 1.5 percent of the sample. These data are thereby consistent with the X-ray diffraction data which showed no LiF, $MnCl_2$, or $MnBr_2$ in the samples. The analysis did provide expected lithium and manganese concentrations but effectively did not account for the active fluorine. A second approach to analysis by neutron activation analysis for Mn, F, and Br differed from the results obtained by wet chemical analysis by showing higher fluorine content.

The possibility of hydrolysis of the samples during handling is a plausible explanation for the analysis discrepancy. This possibility is consistent with the weight change during synthesis, the chemical reactivity of the resulting products, and the weight change on decomposition of $LiMnF_5$, as will be discussed later.

$LiMnF_5$ was found to be compatible with more fuels than the other reactants, as shown in table 19, but was not completely compatible with Mg_3N_2 nor Ca_3N_2. No significant endotherms were noted for $LiMnF_5$ mixtures up to the DTA limit of 500 C; however, decomposition could have occurred without an appreciable temperature change. Exotherms were noted with NaN_3, AlN, and Ca_3N_2. Upon mixing $LiMnF_5$ with either Mg_3N_2 or Ca_3N_2, some sparks were noted and in some cases the mixture would glow brightly for a few seconds.

A series of atmospheric pressure ignition and combustion tests was made with tamped mixtures of $LiMnF_5$ and selected fuels as shown in table 20. Complete combustion was obtained with a 90 weight percent $LiMnF_5$/10 weight percent NaN_3 mixture; however, a 95 weight percent $LiMnF_5$/4 weight percent NaN_3/1 weight percent Al composition would not sustain combustion. With magnesium as the fuel, sustaining combustion occurred with 5 weight percent Mg, but 2.5 weight percent Mg showed marginal combustion behavior.

46

TABLE 19. DTA OF LiMnF$_5$ AND VARIOUS FUELS

Test No.	Fuel	Fuel Weight Percent	LiMnF5, (weight percent)	Endotherms, (C)	Exotherms, (C)
1	NaN$_3$	10.2	89.8	-	124s
2	AlN	5.0	95.0	-	287vw
3	Al	5.2	94.8	-	-
4	Ca$_3$N$_2$	5.5	94.5	-	106wm
5	Li$_3$N	5.7	94.3	-	-
6	Mg	2.5	97.5	-	-
7	Mg	5.0	95.0	-	-
8	NaN$_3$	9.8	90.2	-	123s

NOTE: s = strong, wm = weak to medium, vw = very weak

Similarly, a 5 weight percent Al mixture burned well and a 2 weight percent Al composition did not. An AlN-LiMnF$_5$ mixture and an Fe-LiMnF$_5$ mixture both showed activity upon ignition but failed to sustain combustion.

Based on the ignition and combustion data, sensitivity tests were performed with a 90 weight percent LiMnF$_5$/10 weight percent NaN$_3$ composition and exhibited an impact sensitivity of 150 kg-cm and no friction sensitivity. A 95 weight percent LiMnF$_5$/5 weight percent Mg composition gave an impact sensitivity of 92.3 kg-cm and no friction sensitivity.

Difficulties encountered during preparation of LiMnF$_5$-NaN$_3$ grains were counter to the reasonable impact sensitivities noted above. Three of five NaN$_3$ grain preparations ignited during the pressing operation and burned to completion in the press. As noted in table 21, a 5 weight percent NaN$_3$ grain, successfully prepared, would not sustain combustion in the configuration tested. At 7.5 weight percent NaN$_3$, combustion could be obtained as noted in test No. 5. The exhaust from this test was passed through KI solution but since the KI-F$_2$ reaction is not quantitative, the

TABLE 20. IGNITION AND COMBUSTION TESTS OF LiMnF$_5$ AND VARIOUS FUELS

Test No.	Fuel	Fuel Weight Percent	LiMnF$_5$, (weight percent)	Results
1	Mg$_3$N$_2$	10.2	89.8	Ignition occurred, combustion sustained
2	Mg$_3$N$_2$	10.3	89.7	Sparks, red gas evolved on mixing
3	NaN$_3$	10.1	89.9	Easy ignition, flame front moved evenly at moderate rate
4	NaN$_3$	4.0	95.0	Not self-sustaining combustion
	Al	1.0		
5	Ca$_3$N$_2$	5.3	94.7	Red gas evolved on mixing; no visible combustion
6	Mg	5.1	94.9	Mixture ignited and burned rapidly, combustion complete
7	Mg	2.5	97 5	Partial combustion through center
8	Al	5.1	94.9	Easy ignition, combustion complete - fairly rapid burning rate
9	Al	2.0	98.0	Not self-sustaining combustion
10	AlN	5.4	94.6	Not self-sustaining combustion
11	Fe	4.9	95.1	Not self-sustaining combustion

48

TABLE 21. GRAIN COMBUSTION TESTS OF $LiMnF_5$ AND VARIOUS FUELS

Test No.	Fuel	Fuel Weight Percent	$LiMnF_5$ (weight percent)	Grain Weight, (g)	Grain Length, (in.)	Grain Density, (g/cc)	Burning Rate, (in./sec)	Glass Vessel, (1 atm)	Chamber Pressure, (psi)	Remarks
1	NaN_3	5.0	95.0	8.367	.47	1.72	-	-	X	Grain failed to burn, charred beneath igniter
2	NaN_3	10.0	90.0	-	-	-	-	-	-	Spontaneous ignition during pressing
3	Mg	2.5	97.5	11.864	.54	2.11	-	X	-	Grain burned only near nichrome igniter wire
4	Mg	2.5	97.5	9.542	.60	1.52	-	X	-	Grain heated 150 C, very low burning rate; combustion complete
5	NaN_3	7.5	92.5	10.069	.61	1.60	-	X	-	Fired at ambient temperature, combustion essentially complete, fairly rapid burning rate
6	Mg	2.5	97.5	12.684	.70	1.73	-	X	-	Grain heated 150 C, center of grain combusted
7	NaN_3	7.5	92.5	-	-	-	-	-	-	Spontaneous ignition during pressing
8	NaN_3	7.5	92.5	-	-	-	-	-	-	Spontaneous ignition during pressing
9	Mg	2.5	97.5	14.458	.82	1.69	-	X	-	Ignited easily, but only approximately 1/4-in. of grain burned

1.77 percent yield of fluorine from the grain based on evolved iodine is only an indication of fluorine generation.

Four grains were prepared from a 97.5 weight percent $LiMnF_5$/2.5 weight percent Mg composition. Two grains were tested at ambient temperature and pressure. The $LiMnF_5$ used for the first grain was prepared from the $LiF-MnCl_2-BrF_3$ reaction. The second grain, prepared with $LiMnF_5$ from the $LiF-MnBr_2-BrF_3$ reaction, appeared to ignite easier but in neither case was sustained combustion obtained. Two grains, prepared with $LiMnF_5$ from the $LiF-MnCl_2-BrF_3$ reaction, were fired at ambient pressure and at an elevated temperature of 150 C. The first grain ignited and burned completely but the burning rate was very low. The combustion gas products were swept into a KI solution with nitrogen. The liberated iodine calculated to be a 1.24 percent fluorine yield. The second grain ignited and combustion occurred in the center of the grain.

A sample of $LiMnF_5$ was exposed to air to determine the magnitude of the hydrolysis rate. A sample of CoF_3 of essentially the same weight was examined for comparison. Weight changes were taken as a measure of hydrolysis. Both samples appeared to reach a maximum weight increase after 20 to 24 hours, as shown in figure 5, and in the case of $LiMnF_5$, subsequent exposure caused a loss in weight. The conclusion which can be drawn is that $LiMn_5$ hydrolyzes slowly in air at a rate somewhat like that of CoF_3.

The thermal decomposition of $LiMnF_5$ was investigated under vacuum conditions. A sample was placed under a continuously maintained vacuum and the weight loss was measured at various temperatures. The data are listed in table 22. There was an initial weight loss at ambient temperature that could be interpreted as loss of residual BrF_3. The greatest weight loss occurred at 170 F and above; thus, $LiMnF_5$ appears to be fairly stable to thermal decomposition. After heating for a total of 20.7 hours at temperature levels of 125, 175, 225, and 300 F, 13.35 percent of the weight of the sample was lost. Correcting this value for the ambient temperature weight loss, the resulting figure of 12.24 percent corresponds closely to the value attributable to the loss of one fluorine (12.1 percent) from $LiMnF_5$.

50

TABLE 22. VACUUM[a] DECOMPOSITION OF LiF-MnBr$_2$-BrF$_3$ REACTION PRODUCT

Sample Weight = 4.568 g
Reactor Weight = 528.55 g

Time, (min)	Temperature, (F)	Weight Loss, (g)	Cumulative Weight Loss, (g)	Percent Sample
0	71	-	-	-
30	71	.030	.030	.66
60	71	.010	.040	.88
90	71	.007	.047	1.02
120	71	.004	.051	1.12
150	125	.014	.065	1.42
180	124	.012	.077	1.69
210	122	.022	.099	2.17
240	155	.029	.128	2.80
270	174	.112	.240	5.25
300	176	.037	.277	6.06
330	170	.016	.293	6.41
360	223	.035	.328	7.18
390	224	.014	.342	7.49
420	224	.008	.350	7.66
450	224	.009	.359	7.86
480	224	.003	.362	7.92
550	225	.014	.376	8.23
600	225	.006	.382	8.36
630	282	.013	.395	8.65
660	300	.066	.461	10.09
690	302	.070	.531	11.62
720	300	.020	.551	12.06
750	300	.012	.563	12.32
780	296	.008	.571	12.50
840	296	.010	.581	12.72
900	298	.006	.587	12.85
960	298	.006	.593	12.98
1020	302	.002	.595	13.03
1140	302	.007	.602	13.18
1200	297	.005	.607	13.29
1245	297	.003	.610	13.35

[a] Pressure of 200 microns.

51
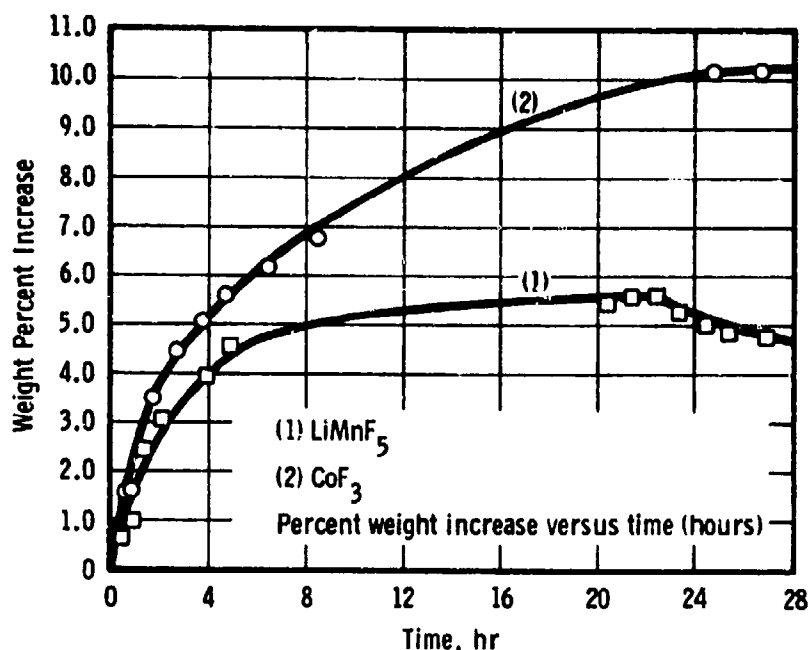
Figure 5. Air Hydrolysis Study

TASK 3: SCALABILITY TESTING AND SUPPORTING ANALYSIS

The objective of this task was to examine the scalability of the fluorine gas generation systems which were recommended as a consequence of the work of task 2. A specific objective of the program was development of a design of a generator producing .25 lb/sec of fluorine for a period of from 1 to 5 sec. An additional generator producing 5 lb/sec of fluorine for 10 sec was also designed.

During task 2 of the program, all candidates with the exception of $LiMnF_5$ had been eliminated from consideration on the basis of production of interfering or deactivating species. $LiMnF_5$, on the other hand, produces essentially pure fluorine in the gas phase with the remainder forming a solid sintered residue. The fluorine yield of approximately 10 percent by weight is offset by the high purity of the fluorine available.

The results of task 2 showed that the fluorine-generating solid grains exhibited a uniformly low burning rate with only a modest pressure exponent. At approximately 100 psia, the burning rates of these gas generator grains were in the range of approximately .02 to .03 in./sec. At 1000 psia the

burning rate would typically be of the order of .05 in./sec. To utilize
materials with such low burning rates at the flow rates and times specified
in any reasonable geometry required a different design than normally
considered in conventional gas generators. A solution to this type of system
is the incorporation of discrete particles or pellets of the gas generator in
a packed bed configuration with an igniter sized to ignite the entire bed.
In this manner, high flow rates can be achieved through the large surface
area available with the discrete particles. To achieve similar results with
normal grain designs would require abnormally thin webs which are
inconsistent with the physical properties of this type of gas generator.

The ignition of the pellet bed requires a more elaborate and effective
technique than the experimental methods employed in the pressed grain
experiments conducted earlier in the program. Although the hot wire type of
igniter could eventually accomplish the ignition of all the gas generator
material, extensive ignition delays and long rise times would be the
consequence. A more appropriate ignition procedure involves a device
producing a reactive gas with hot particles entrained to initiate combustion
in a large fraction of the particles in the pellet bed. The hot particles
serve to ignite a large number of pellets initially while the reactive gas
serves to pressurize the system to promote combustion as well as to propagate
the ignition by reaction with additional pellets.

In the case of the design point with the lower flow rates and shorter
burning time, an igniter was employed which consisted of a fluorine gas
generating formulation which burned at a higher temperature than the main gas
generation grains. This material was a $KBrF_6$ formulation and was selected to
produce a minimum of contamination during the ignition stage as well as its
high temperature. The igniter stage was initiated by an electric squib
initiator. In the case of the larger generator producing 5 lb of fluorine
per second, an additional ignition stage was incorporated consisting of the
standard fluorine gas generator formulation but with finer particle size to
enhance mass flow rate. This stage was employed between the igniter grain
and the gas generator grain. The design drawings for the generators are
shown in figures 6 and 7, respectively.

53
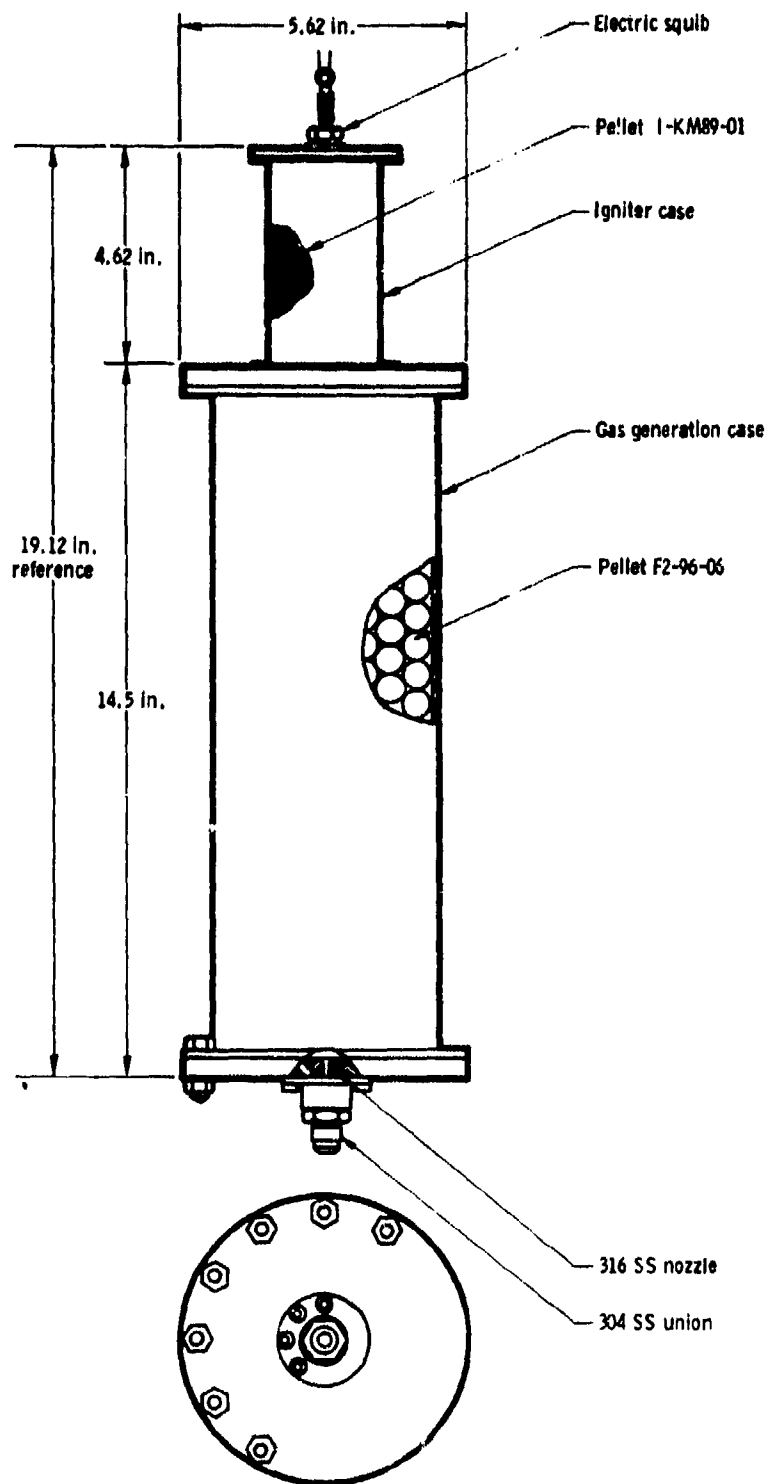
Figure 6.   Smaller-Scale Fluorine Gas Generator Design
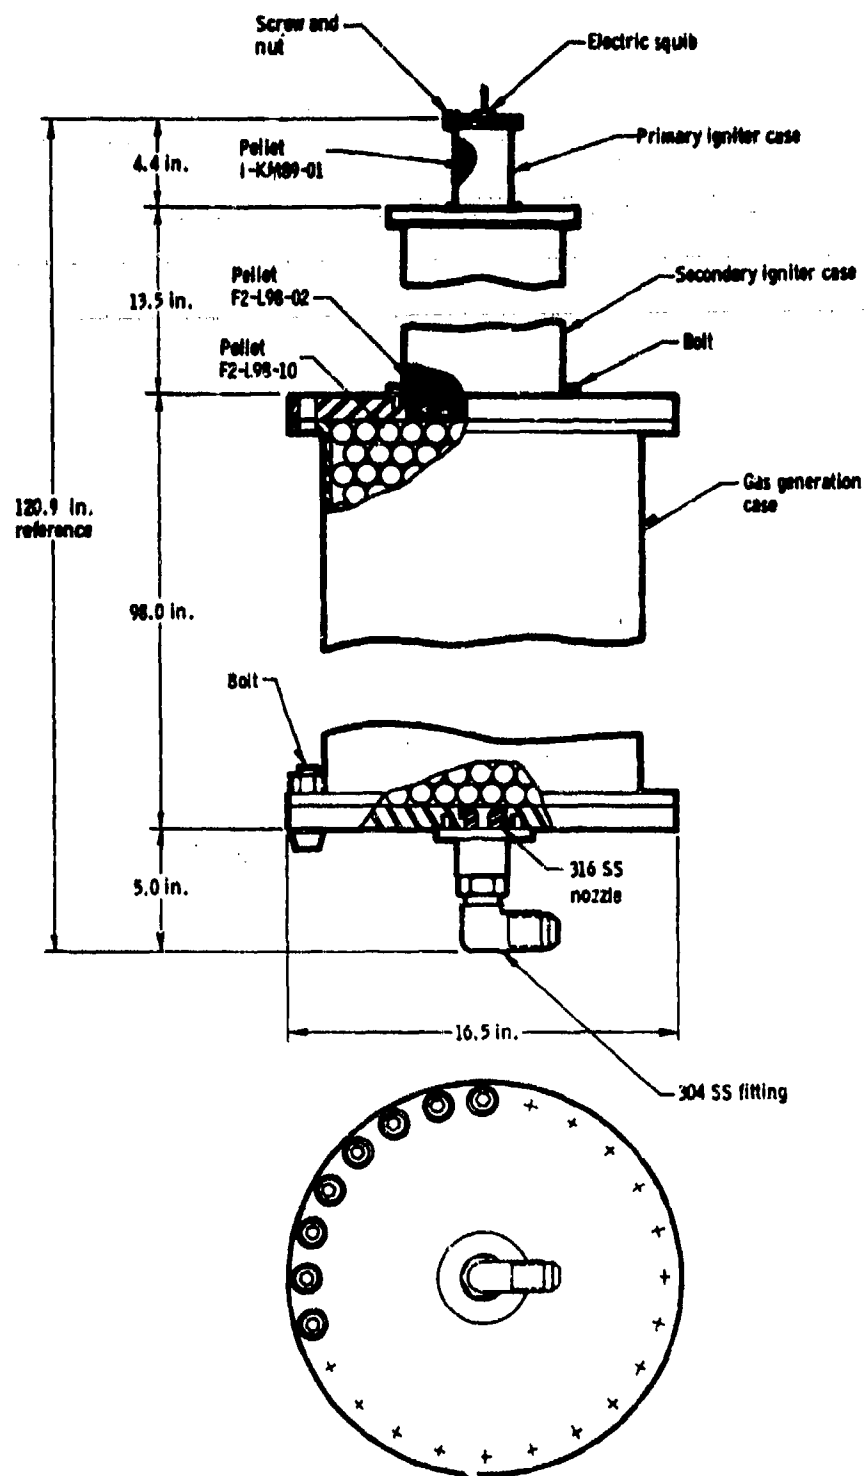
Figure 7.   Larger-Scale Fluorine Gas Generator Design

Inconel-718 was selected for the material of construction since it embodied the best combination of properties required for the design requirements. It resists corrosion by fluorine and is frequently employed for this purpose. It further exhibits good strength-temperature relationships and should be adequate for the times involved in the requirements. Further, it is less expensive than other materials such as nickel which are sometimes employed to resist fluorine corrosion.

No filters are shown in the design sketches. These are conceived of as separate packages and, in view of the tendency of the gas generator grain to form a self-filtering clinker, may be of minimum size.

CONCLUSIONS

The exploratory program described in this report was aimed at defining fluorine reactant systems from available or easily synthesized compounds that could be considered for chemical laser operations. The impact of the exhaust composition from candidate gas generators on overall laser system size and performance could not be quantitatively defined for many of the compositions considered in the program; therefore, subjective evaluations were made to reduce the number of candidates to a workable number consistent with the scope of the program.

The conclusions that can be drawn from the work reported earlier are as follows:

A. As a result of an in-depth literature review, a series of 32 candidate reactants were identified that potentialy met the minimum requirements for fluorine generation of 10 weight percent fluorine. Of these, 22 also potentially met the goal of 25 weight percent fluorine.

B. A list of 13 candidate reactants were identified that met realistic performance criteria primarily involving safety, stability, and cost. A large number of the original 32 candidates were rejected for safety considerations.

C. Of five reactants selected for experimental evaluation, small-scale grains were prepared and tested using $KBrF_6$, $KClF_4$, and $LiMnF_5$ as the fluorine-generating ingredient. Satisfactory combustion and ignition of $KBrF_6/Mg_3N_2$ and $KClF_4/AlN$ reactant systems was demonstrated.

D. A low-cost, one-step route for the preparation of $LiMnF_5$ was established. The compound was determined to be stable to decomposition under vacuum at temperatures up to approximately 160 F. Low hydrolysis rates observed in air were in agreement with the low apparent reactivity observed upon adding $LiMnF_6$ to water.

E. The compatibility of $LiMnF_5$ with various fuels was demonstrated. Ignition and combustion studies showed the feasibility of developing $LiMnF_5$ reactant systems that produce only fluorine as a

gaseous product. The fluorine yield for the candidate formulations is of the order of 10 weight percent.

F.   The design of a fluorine gas generator using a LiMnF$_5$/Mg composition showed the ignition system to be the area of greatest importance in scale-up.

BIBLIOGRAPHY

1. Flanagan, J. E., K. O. Christe and D. Pilovich, et al., "Solid Propellant Laser Fuel Generator," (C), Report No. AFWL-TR-73-195, Rockwell International, Canoga Park, Calif., Nov. 1973.

2. W. H. Schechter, U.S. Patent 2,469,414 (1949).

3. Matthews, D. R., "Emergency Destruction of Classified Material," Contract N00014-72-C-0031, Final Report No. 2527-FTR, Chemical Systems Division; Sept. 1974.

4. Sauer, D. T., R. B. Leining, G. M. Daurelle, and K. L. Harvey, "Solid Fueled Generator for Fluorinated Gases," Tri-Service Chemical Laser Symposium, 18-20 Feb. 1976, Kirtland AFB, N. M.

5. Flanagan, J., "Solid Fluorine Generator Development," Tri-Service Chemical Laser Symposium, 18-20 Feb. 1976, Kirtland AFB, N. M.

6. Goetschel, C. T., V. A. Campanile, R. M. Curtis, K. R. Loos, C. D. Wagner and J. N. Wilson, Inorg. Chem. 11 (7), 1696-1701 (1972).

7. Zemva, B. and J. Slivnik, Vestn. Slov. Kem. Drus., 19 (1-4), 43-6 (1972).

8. Moody, G. J. and H. Selig, Inorg. Nucl. Chem. Letters, 2 (10), 319 (1966).

9. Klimov, V. D., V.N. Prusakov and V. B. Sokolov, (USSR), Dokl. Akad. Nauk. SSSR, 217 (5), 1077-9 (1974).

10. Whitney, E., R. MacLaren, T. Hurley and C. Fogle, J. Am. Chem. Soc., 86, 4340 (1964).

11. Christe, K. O., and J. P. Guertin, Inorg. Chem., 5 (3), 473-6 (1966).

12. Aubert, J. and G. H. Cady, Inorg. Chem., 9 (11), 2600-2 (1970).

13. Pullen, K. E. and G. H. Cady, Inorg. Chem., 5 (11), 2057-9 (1966).

14. Moody, G. J. and H. Selig, Inorg. Nucl. Chem. Letters, 2, 319 (1966).

15. Prusakov, V. N., V. B. Sokolov, and B. B. Chaivanov, (USSR), Zh. Fiz. Khim., 45 (5), 1102-5 (1971).

16. Selig, H., Science, 144, (3618) 537 (1964), cf. Sci. Am., 210, 66-67 (1964).

17. Guertin, J. P., K. O. Christe and A. E. Pavlath, Inorg. Chem., 5(11), 1921-24, (1966).

18. Christe, K. O., J. P. Guertin and A. E. Pavlath, Inorg. Nucl. Chem. Letters, 2, 83 (1966).

19. Tolberg, W. E., R. T. Rewick, R. S. Stringham, and M. E. Hill, Inorg. Chem., 6, 1156 (1967).

20. Bouy, P., Ann. Chem. (Paris), 13 (4), 853-90, (1959).

21. Whitney, E., R. MacLaren, C. Fogle and T. Hurley, J. Am. Chem. Soc., 86, 2583 (1964).

22. Sukornick, B., C. A. Wamser, (Allied Chemical Corp.), U.S. 3,422,159,(CL 260-648), 14 Jan. 1969, 4 pp.

23. Christe, K. O. and W. Maya, Inorg. Chem., 8 (6), 1253-7 (1969).

24. Chretien, A. and P. Bouy, Compt. Rend., 246, 2493-5 (1958).

25. Burns, J. H., R. D. Ellison and H. A. Levy, Acta. Cryst., 18 (1), 11-16 (1965).

26. Ogrin, T., M. Bohine and J. Slivnik, J. Chem. Eng. Data, 18 (4), 402 (1973).

27. Gillespie, R. J. and G. J. Schrobilgen, Inorg. Chem., 13 (4), 765-70 (1974).

28. Gillespie, R. J. and G. J. Schrobilgen, Inorg. Chem., 13 (5), 1230-5 (1974).

29. Christe, K. O. and R. D. Wilson, Inorg. Chem., 14 (3), 694-6 (1975).

30. Sharpe, A. G. and A. A. Woolf, J. Chem. Soc., 1951, 798-801.

31. Hoppe, R., W. Dähne and W. Klemm, Ann. Chem. (Paris), 658, 1-5 (1962).

32. Hoppe, R., W. Dähne, and W. Klemm, Naturwissenshaften, 48, 429 (1961).

33. Tolberg, W. E., R. T. Rewick, R. S. Stringham, and M. E. Hill, Inorg. Nucl. Chem. Letters, 2, 79 (1966).

34. Christe, K. O., R. D. Wilson, and A. E. Axworthy, Inorg. Chem., 12 (10), 2478-81 (1973).

35. Young, A. R. and D. Moy, Inorg. Chem., 6 (1), 178-9 (1967).

36. Zemva, B., J. Zupan, and J. Slivnik, Inst. Jozef Stefan, IJS, Rep. R-585, 4 pp. (1970).

37. Zemva, B., and J. Slivnik, Inst. Jozef Stefan, IJS, Rep. R-589, 12 pp. (1970).

38. Zemva, B., and J. Slivnik, J. Inorg. Nucl. Chem., 33(11), 3052-3,(1971).

39. Legasov, V. A., A. S. Marinin (USSR), Zh. Fiz. Khim., 46 (9), 2420-1 (1972).

40. Selig, H., and J. Shamir, Inorg. Chem., 3, 294 (1964).

41. Pilipovich, D., C. B. Lindahl, C. J. Schack, R. D. Wilson, and K. O. Christe, Inorg. Chem., 11 (9), 2189-92 (1972).

42. Peacock, R. D., J. Chem. Soc., 1953, 3617-19.

43. Hoppe, R., W. Liebe, and W. Dähne, Z. anorg. allgem. Chem., 307, 276 (1961).

44. Woolf, A. A., J. Chem. Soc., 1950, 1053-6.

45. Sharp, D. W. A. and J. Thorley, J. Chem. Soc., 1963, 3557-60.

APPENDIX A
REACTANTS CONSIDERED LIST

The reactants considered list is composed of five tables depicting the properties of 32 candidate reactants. Table A-1 consists of a summary of the results of thermochemical equilibrium calculations conducted at temperatures of 300, 1000, 1500, and 2000 K and 1 atm pressure. These computer calculations effectively described the products of equilibrium dissociation of each reactant at each of the four designated temperatures. The data tabulated for each candidate include the weight percent fluorine available as F, F_2, and NF_3, and the α at 1500 K. Table A-2 contains the more important physical properties such as melting point, vapor pressure, decomposition temperature, preparation temperature, and heat of formation as well as chemical properties such as chemical reactivity and overall stability. These data were summarized from the literature. The decomposition temperature was generally that temperature where the material was reported to exhibit an appreciable dissociation pressure. The reported preparation temperatures were listed since, in some instances, these values depicted the overall thermal stability where more direct data were lacking. The heats of formation were estimated in many instances and are so noted.

Table A-3 lists availability data, the most common synthesis routes, and estimated costs for preparation of various quantities of each reactant from 10 to 10,000 lb. The availability assessment was made on a comparative basis of the commercial availability of precursors in the synthesis of each reactant and the complexity of synthesis. Costs were estimated based on labor and raw material costs only. As such, these costs presume existence of manufacturing facilities (e.g., no capitalization costs) and also do not include costs for process development. As a result, these costs are significantly less than can be expected, particularly for the very limited quantities included in this survey, and are presented for comparison purposes only.

Table A-4 is devoted to the properties which relate to potential hazards associated with the preparation and uses of the materials. These properties

include the reactivity with dry or moist air, the toxicity of precursors, and toxicity of the decomposition products. The data for this table were obtained from information developed from the literature search.

Table A-5 consists of a summary compilation of the thermochemical calculations of candidate reactant systems performed to evaluate the primary performance parameters of theoretical flame temperature, product composition, and weight percent fluorine.

TABLE A-1. FLUORINE YIELD OF REACTANTS
(RCL-1)

Reactant No.	Reactant Composition	Fluorine Yield, (weight percent)				γ 1500 K	
		300 K	1000 K	1500 K	2000 K		
1	NF_4BF_4	53.72	53.72	53.72	53.72	1.152	
2	XeF_6	46.47	46.47	46.47	46.47	1.159	
3	$2NOF \cdot XeF_6$	18.46	37.60	43.81	44.24	1.167	
4	$KrF_2 \cdot XeF_6$	41.40	41.40	41.40	41.40	1.168	
5	$NOClF_4$	6.25	32.34	39.97	45.13	1.177	
6	$4XeF_6 \cdot MnF_4$	41.00	42.68	42.68	42.72	1.155	
7	$4XeF_6 \cdot SnF_4$	38.78	38.78	38.78	38.78	1.157	
8	$NOF \cdot XeOF_4$	19.65	34.40	40.10	40.51	1.177	
9	$XeF_2 \cdot 2BrF_5$	7.32	15.75	36.03	38.26	1.140	
10	$XeF_6 \cdot BF_3$	36.41	36.41	36.41	36.41	1.160	
11	NF_4AsF_6	34.06	34.06	47.23	47.68	1.120	
12	$(NO)_2MnF_6$	0	15.64	24.18	24.93	1.156	
13	$KBrF_6$	16.30	30.94	32.06	34.66	1.095[a]	
14	$NF_3O \cdot SbF_5$	8.49	15.18	18.55	18.75	1.129	
15	$NOBrF_4$	0	3.89	29.82	33.38	1.149	
16	$XeF_2 \cdot XeF_4$	30.27	30.27	30.27	30.27	—	
17	BrF_6AsF_6	9.93	15.52	38.98	40.65	1.118	
18	$NOAsF_6$	0	4.85	25.42	26.02	1.124	
19	NF_4SbF_6	29.16	29.16	29.16	29.16	1.131	
20	$N_2F_3AsF_6$	27.74	27.74	41.23	41.62	1.125	
21	$RbBrF_6$	0	8.19	26.81	28.91	1.148	
22	$KClF_4$	0	24.89	25.29	30.42	1.095[a]	
23	ClF_2BF_4	0	23.49	23.77	28.52	1.166	
24	$ClF_3O \cdot BF_3$	0	21.39	21.62	26.18	1.175	
25	$CsBrF_6$	0	7.00	22.91	24.71	1.140	
26	XeF_2	22.45	22.45	22.45	22.45	1.195	
27	$NOVF_6$	—	5.80	18.17	19.48	1.103	X
28	$XeF_2 \cdot MnF_4$	—	18.97	18.77	19.03	1.153	X
29	$XeF_2 \cdot VF_5$	—	12.36	17.32	18.02	1.113	X
30	MnF_4	—	14.50	14.23	14.63	1.077[a]	X
31	$LiMnF_5$	—	12.10	11.87	12.27	1.074[a]	X
32	$KMnF_5$	—	10.04	9.85	10.15	1.075[a]	X

[a]Includes condensed phases.

65

TABLE A-2. STABILITY OF REACTANTS (RCL-2)

Reactant No.	Reactant composition	Melting point (C)	Prep. temperature (C)	Decomposition temperature, (C)	ΔH°_f (kcal/mole)	Vapor pressure	Chemical reactivity	Overall stability	
1	NF_4BF_4	–	-196 (by irradiation)	>250	-337.4	nil at 25 C	Very reactive, strong oxidizer	Good in dry air, reacts with H_2O	(X)
2	XeF_6	49.5	120	bp. 75.6	-96.9	23.4mm Hg at 22.7 C	Stronger oxidizer than XeF_2 or XeF_4	Reacts with glass, hazardous with H_2O	
3	$2NOF \cdot XeF_6$	>130	–	–	(-149)	~40 mm Hg at 25 C	Extremely reactive	Hazardous with H_2O; fair stability	
4	$KrF_2 \cdot XeF_6$	40±2	20	~25	(-101)	11mm Hg at 20 C	Comparable to XeF_6	Hazardous with H_2O; poor stability	X
5	$NOClF_4$	–	-23	<0	-69.2	1.4 atm at 0 C	Comparable to ClF_3	Reacts with glass, H_2O; poor stability	
6	$4XeF_6 \cdot MnF_4$	–	225	>40	(-659)	loses XeF_6 at 40 C in vac	(Comparable to XeF_6)	(Hazardous with H_2O; poor stability)	
7	$4XeF_6 \cdot SnF_4$	–	57	106	(-679)	loses XeF_6 at 50 C in vac	Strong oxidizer, fluorinating agent	(Hazardous with H_2O; fair stability)	
8	$NOF \cdot XeOF_4$	40	–	~30	(-42)	30mm Hg at 23 C	(Very reactive)	(Hazardous; poor stability)	(X)
9	$XeF_2 \cdot 2BrF_5$	~-23	–	–	(-275)	–	(Very reactive)	Unknown, poor melting point	X
10	$XeF_6 \cdot BF_3$	90	25	–	(-394)	<1mm Hg at 25 C	Comparable to XeF_6	(Hazardous with H_2O; poor stability)	
11	NF_4AsF_6	–	200	~270	(-335)	nil at 25 C	Very reactive, strong oxidizer	Good; corrosive, reacts with H_2O	
12	$(NO)_2MnF_6$	–	100	150	(-317)	nil at 25 C	(Comparable to NOF)	Good; corrosive, reacts with H_2O	
13	$KBrF_6$	–	100	~250	(-252)	nil at 25 C	Comparable with BrF_5	Good; corrosive, reacts with H_2O	
14	$NF_3O \cdot SbF_5$	–	–	>25	(-371)	–	Strong oxidizer	(H_2O reactive)	
15	$NOBrF_4$	225	20	>100	(-98.6)	Some vp at 100 C	Strong oxidizer, very reactive	Good, corrosive, reacts with H_2O	
16	$XeF_2 \cdot XeF_4$	90.2	340 to 380	>25	(-103)	Some vp at 25 C	Comparable to XeF_4	(Hazardous with H_2O; fair stability) (Good stability;	

No.	Compound								
10	XeF$_6$·BF$_3$	90	25	—	(-394)	<1mm Hg at 25 C	Comparable to XeF$_6$	(Hazardous with H$_2$O; poor stability)	
11	NF$_4$AsF$_6$	—	200	~270	(-335)	nil at 25 C	Very reactive, strong oxidizer	Good; corrosive, reacts with H$_2$O	
12	(NO)$_2$MnF$_6$	—	100	150	(-317)	nil at 25 C	(Comparable to NOF)	Good; corrosive, reacts with H$_2$O	
13	KBrF$_6$	—	100	~250	(-252)	nil at 25 C	Comparable with BrF$_5$	Good; corrosive, reacts with H$_2$O	
14	NF$_3$O·SbF$_5$	—	—	>25	(-371)	—	Strong oxidizer	(H$_2$O reactive)	
15	NOBrF$_4$	225	20	>100	(-98.6)	Some vp at 100 C	Strong oxidizer, very reactive	Good, corrosive, reacts with H$_2$O	
16	XeF$_2$·XeF$_4$	90.2	340 to 380	>25	(-103)	Some vp at 25 C	Comparable to XeF$_4$	(Hazardous with H$_2$O; fair stability)	
17	BrF$_6$AsF$_6$	—	low to 25	>20	(-370)	Stable in vac at 20 C	Very strong oxidizer	(Good stability; corrosive; reacts with H$_2$O)	
18	NUAsF$_6$	—	94	>100	(-241)	Some vp at 200 C	Very reactive	Good; reacts with H$_2$O	
19	NF$_4$SbF$_6$	—	200	200	(-403)	Slight at 200 C	Very strong oxidizer	Good; reacts with H$_2$O, corrosive	
20	N$_2$F$_3$AsF$_6$	—	-78 to 25	>25	(-269)	nil at 25 C	(Very strong oxidizer)	(Fair; corrosive, reacts with H$_2$O)	
21	RbBrF$_6$	—	100	~300	(-252)	nil at 25 C	Very strong oxidizer, comparable to BrF$_5$	Good; reacts with H$_2$O, corrosive	
22	KClF$_4$	—	100	200	(-187)	nil at 25 C	Strong oxidizer, comparable to ClF$_3$	Good, reacts with H$_2$O, corrosive	x
23	ClF$_2$BF$_4$	30	-78 to 25	~10	-334.1	550mm Hg at 5 C	Strong oxidizer, comparable to ClF$_3$	Poor; high dissociation pressure	
24	ClF$_3$O·BF$_3$	—	-196 to 25	>20	(-326)	nil at 20 C	Comparable to ClF$_3$	(Good; reactive)	
25	CsBrF$_6$	—	100	300	(-252)	nil at 25 C	Strong oxidizer, comparable to BrF$_5$	Good; corrosive, high reactivity	
26	XeF$_2$	~140	400	~25	-40.5	4.55mm Hg at 25 C	Good oxidizer	Fair; high vapor pressure	(X)
27	NOVF$_6$	—	20	60	-396.2	—	Strong oxidizer, similar to NOF	Good; reacts with H$_2$O	
28	XeF$_2$·MnF$_4$	—	120	—	(-286)	—	(Comparable to MnF$_4$)	(Good; reacts with H$_2$O)	
29	XeF$_2$·VF$_5$	38	90	>90	(-409)	<5mm Hg at 25 C	Potentially strong oxidizer	(Fair)	
30	MnF$_4$	—	550	~25	(-230)	—	Strong fluorinating agent	Fair; reacts with H$_2$O	(X)
31	LiMnF$_5$	—	350	—	(-371)	nil at 25 C	(Comparable to MnF$_4$)	(Good, reacts with H$_2$O)	
32	KMnF$_5$	—	20	~180	(-381)	nil at 25 C	Comparable to MnF$_4$	(Good; reactive)	

No.	Compound								X
15	$NOBrF_4$	225	20	>100	(-98.6)	Some vp at 100 C	Strong oxidizer, very reactive	Good; corrosive, reacts with H_2O	
16	$XeF_2 \cdot XeF_4$	90.2	340 to 380	>25	(-103)	Some vp at 25 C	Comparable to XeF_4	(Hazardous with H_2O; fair stability)	
17	BrF_6AsF_6	—	low to 25	>20	(-370)	Stable in vac at 20 C	Very strong oxidizer	(Good stability; corrosive; reacts with H_2O)	
18	$NOAsF_6$	—	94	>100	(-241)	Some vp at 200 C	Very reactive	Good; reacts with H_2O	
19	NF_4SbF_6	—	200	200	(-403)	Slight at 200 C	Very strong oxidizer	Good; reacts with H_2O, corrosive	
20	$N_2F_3AsF_6$	—	-78 to 25	>25	(-269)	nil at 25 C	(Very strong oxidizer)	(Fair; corrosive, reacts with H_2O)	
21	$RbBrF_6$	—	100	~300	(-252)	nil at 25 C	Very strong oxidizer, comparable to BrF_5	Good; reacts with H_2O, corrosive	
22	$KClF_4$	—	100	200	(-187)	nil at 25 C	Strong oxidizer, comparable to ClF_3	Good, reacts with H_2O, corrosive	
23	ClF_2BF_4	30	-78 to 25	~10	-334.1	550mm Hg at 5 C	Strong oxidizer, comparable to ClF_3	Poor; high dissociation pressure	x
24	$ClF_3O \cdot BF_3$	—	-196 to 25	>20	(-326)	nil at 20 C	Comparable to ClF_3	(Good; reactive)	
25	$CsBrF_6$	—	100	300	(-252)	nil at 25 C	Strong oxidizer, comparable to BrF_5	Good; corrosive, high reactivity	
26	XeF_2	~140	400	~25	-40.5	4.55mm Hg at 25 C	Good oxidizer	Fair; high vapor pressure	(X)
27	$NOVF_6$	—	20	60	-396.2	—	Strong oxidizer, similar to NOF	Good; reacts with H_2O	
28	$XeF_2 \cdot MnF_4$	—	120	—	(-286)	—	(Comparable to MnF_4)	(Good; reacts with H_2O)	
29	$XeF_2 \cdot VF_5$	38	90	>90	(-409)	<5mm Hg at 25 C	Potentially strong oxidizer	(Fair)	
30	MnF_4	—	550	~25	(-230)	—	Strong fluorinating agent	Fair; reacts with H_2O	
31	$\underline{Li}MnF_5$	—	350	—	(-371)	nil at 25 C	(Comparable to MnF_4)	(Good, reacts with H_2O)	(X)
32	$KMnF_5$	~	20	~180	(-381)	nil at 25 C	Comparable to MnF_4	(Good; reactive)	

Parentheses indicate estimated properties

TABLE A-3. REACTANT AVAILABILITY AND COST (RCL-3)

Reactant No.	Reactant Composition	Availability	Synthesis Route	Cost, ($/lb)				Comments	X
				10 lb	100 lb	1000 lb	10,000 lb		
1	NF_4BF_4	–	$NF_3 + F_2 + BF_3$	>2000	>1000	–	–	Irradiation at -196 C	X
2	XeF_6	C	$Xe + F_2$	1200	800	600	520	33 to 36 atm pressure	(X)
3	$2NOF \cdot XeF_6$	D	$NOF + XeF_6$	920	700	490	410		(X)
4	$KrF_2 \cdot XeF_6$	D	$KrF_2 + XeF_6$	1500	970	720	560	BrF_5 solvent	(X)
5	$NOClF_4$	A	$NOF + ClF_3$	190	118	61	31		
6	$4XeF_6 \cdot MnF_4$	D	$Mn + F_2 + Xe$	1200	780	580	500		(X)
7	$4XeF_6 \cdot SnF_4$	D	$SnF_4 + XeF_6$	1200	750	560	480		(X)
8	$NOF \cdot XeOF_4$	D	$NOF + XeOF_4$	1250	820	650	550		(X)
9	$XeF_2 \cdot 2BrF_5$	D	$XeF_2 + BrF_5$	625	490	320	275		(X)
10	$XeF_6 \cdot BF_3$	C	$XeF_6 + BF_3$	950	725	540	450		(X)
11	NF_4AsF_6	C	$NF_3 + F_2 + AsF_5$	495	355	215	140	35 atm pressure	
12	$(NO)_2MnF_6$	B	$NOF + MnF_3 + BrF_3$	255	165	100	60		
13	$KBrF_6$	B	$KF + BrF_5$	150	100	72	42		
14	$NF_3O \cdot SbF_5$	D	$NF_3O + SbF_5$	190	120	75	50	HF solvent	
15	$NOBrF_4$	A	$NOF + BrF_3$	160	100	54	29		
16	$XeF_2 \cdot XeF_4$	A	$Xe + F_2$ (99.9% Xe) (92.94% Xe)	1400 980	940 750	750 450	640 280	22 to 24 atm pressure	
17	BrF_6AsF_6	C	$Kr_2F_3 \cdot AsF_6 + BrF_5$	290	210	130	90	BrF_5 solvent	
18	$NOAsF_6$	A	$NOF + AsF_5$	275	190	120	85		
19	NF_4SbF_6	B	$NF_3 + F_2 + SbF_5$	270	175	105	78	85 atm pressure	
20	$N_2F_3AsF_6$	B	$N_2F_4 + AsF_5$	770	480	260	165		(X)
21	$RbBrF_6$	A	$RbF + BrF_5$	190	140	95	60		
22	$KClF_4$	B	$KF + ClF_3$	105	70	51	30		

No.	Compound	Avail.	Reaction					Notes	
17	BrF_6AsF_6	C	$Kr_2F_3 \cdot AsF_6 + BrF_5$	290	210	130	90	BrF_5 solvent	(X)
18	$NOAsF_6$	A	$NOF + AsF_5$	275	190	120	85		
19	NF_4SbF_6	B	$NF_3 + F_2 + SbF_5$	270	175	105	78	85 atm pressure	
20	$N_2F_3AsF_6$	B	$N_2F_4 + AsF_5$	770	480	260	165		
21	$RbBrF_6$	A	$RbF + BrF_5$	190	140	95	60		
22	$KClF_4$	B	$KF + ClF_3$	105	70	51	30		
23	ClF_2BF_4	A	$ClF_3 + BF_3$	65	39	26	20		
24	$ClF_3O \cdot BF_3$	B	$ClF_3O + BF_3$	165	109	76	55		
25	$CsBrF_6$	A	$CsF + BrF_5$	175	110	82	57		
26	XeF_2	A	$Xe + F_2$ (99.9% Xe) (92.94% Xe)	1600 795	1100 610	920 390	700 295	BrF_3 solvent	(X)
27	$NOVF_6$	A	$NOCl + V_2O_5$	510	310	160	82		
28	$XeF_2 \cdot MnF_4$	B[a]	$MnF_2 + XeF_2$	840	670	520	430		(X)
29	$XeF_2 \cdot VF_5$	B	$XeF_2 + VF_5$	1220	750	530	440		(X)
30	MnF_4	C	$MnF_3 + F_2$	76	48	34	27		
31	$LiMnF_5$	D	$LiF + MnF_2 + F_2$	105	72	53	32		
32	$KMnF_5$	B	$KMnO_4 + BrF_3$	90	61	45	24		

[a]Yield not reported

Availability Legend:

A: Commercially available or easily synthesized (yield 75%)
B: Synthesis established (yield >50%)
C: Difficult synthesis (yield <50%)
D: Only milligram quantities prepared
F: Synthesis reported, yield and difficulty unknown

Reactant No.	Reactant Composition	Reactivity with		Precursor Toxicity		
		Dry Air	Moist Air	Compound	Threshold Limit Value	Comments
1	NF_4BF_4	None	Forms HF, NF_3, and BF_3	NF_3 BF_3 F_2	29 3	Mildly toxic Irritant Reacts to form H for HF = 2 mg/m
2	XeF_6	None	Forms hazardous products and HF	Xe F_2	N/A .2	Asphyxiant Reacts to form H
3	$2NOF \cdot XeF_6$	(None)	(Forms hazardous products, HF and NOX)	XeF_6 NOF	— —	See XeF_6 Reacts to form H
4	$KrF_2 \cdot XeF_6$	—	(Forms hazardous products and HF)	KrF_2 XeF_6	— —	Reacts to form H See XeF_6
5	$NOClF_4$	None	Forms HF, HCl, and NOX	NOF ClF_3	— .4	Reacts to form H Strong irritant;
6	$4XeF_6 \cdot MnF_4$	(None)	(Forms hazardous products and HF)	XeF_6 MnF_4	— 6	See XeF_6 Dust, causes ner system disorder
7	$4XeF_6 \cdot SnF_4$	(None)	(Forms hazardous products and HF)	XeF_6 SnF_4	— (2)	See XeF_6 Toxic fumes on decomposition
8	$NOF \cdot XeOF_4$	—	(Forms hazardous products and HF)	NOF $XeOF_4$	— —	Reacts to form H (Strong irritant
9	$XeF_2 \cdot 2BrF_5$	—	(Reacts to form HF)	XeF_2 BrF_5	— .4	Toxic; irritant Strong irritant,
10	$XeF_6 \cdot BF_3$	(None)	(Forms hazardous products and HF)	XeF_6 BF_3	— 3	See XeF_6 Irritant
11	NF_4AsF_6	None	Reacts to form HF and toxic products	NF_3 F_2 AsF_5	29 .2 <.1	Mildly toxic Reacts to form H Cumulative pois (chronic system

C

4. REACTANT SAFETY (RCL-4)

Comments		Decomposition Product Toxicity			
		Compound	Threshold Limit Value	Comments	
ly toxic		NF_3	29	Mildly toxic	
tant		BF_3	3	Irritant	
ts to form HF, (TLV HF = 2 mg/m^3)		F_2	.2	Forms HF in moist air	
yxiant		Xe	N/A	Asphyxiant	
ts to form HF		P_2	.2	Forms HF in moist air	X
XeF$_6$		Xe	N/A	Asphyxiant	
ts to form HF, NOX		F_2	.2	Forms HF in moist air	X
		N_2, O_2	N/A	—	
ts to form HF		Kr	N/A	Asphyxiant	
XeF$_6$		Xe	N/A	Asphyxiant	X
		F_2	.2	Forms HF in moist air	
ts to form HF		ClF	(.2)	Forms HCl and HF in moist air	
ng irritant; tcxic		F_2	.2	Forms HF in moist air	
		N_2, O_2	N/A	—	
XaF$_6$		F_2	.2	Forms HF in moist air	
, causes nervous		Xe	N/A	Asphyxiant	X
em disorders		MnF_3	6	Dust causes nervous	
		MnF_2	6	system disorders	
XeF$_6$		Xe	N/A	Asphyxiant	X
c fumes on		F_2	.2	Forms HF in moist air	
mposition		SnF_2	(2)	Forms toxic fumes and	
		SnF_4	(2)	HF in moist air	
ts to form HF		F_2	.2	Forms HF in moist air	X
ong irritant)		Xe	N/A	Asphyxiant	
		O_2, N_2	N/A	—	
c; irritant		F_2	.2	Forms HF in moist air	
ng irritant, toxic		Xe	N/A	Asphyxiant	
		BrF	(.2)	Forms HF and HBr in moist air	
XeF$_6$		Xe	N/A	Asphyxiant	X
tant		F_2	.2	Forms HF in moist air	
		BF_3	3	Irritant	
ly toxic		F_2	.2	Forms HF in moist air	
ts to form HF		N_2	N/A	—	
lative poison		AsF_3	<.1	Cumulative poison	X
onic systemic)		AsF_5	<.1	(chronic systemic)	

b

Reactant No.	Reactant Composition	Reactivity with		Precursor Toxicity		
		Dry Air	Moist Air	Compound	Threshold Limit Value	Comments
12	$(NO)_2MnF_6$	None	Forms HF and other irritants	NOF MnF_4	— 6	Reacts to form HF Dust causes nervous system disorders
13	$KBrF_6$	None	Forms HF and HBr	KF BrF_5	2.5 .4	Dust-irritant Strong irritant, toxic
14	$NF_3O \cdot SbF_5$	(None)	Forms HF and poisonous Sb compounds	NF_3O SbF_5	— .5	Highly toxic LD_{50} = 200 to 500 ppm Cumulative poison (chroni systemic)
15	$NOBrF_4$	None	Forms HF, HBr, NOX	NOF BrF_3	— .4	Reacts to form HF Strong irritant, toxic
16	$XeF_2 \cdot XeF_4$	(None)	(Forms hazardous compounds)	XeF_2 XeF_4	— —	Toxic, irritant Toxic, irritant
17	BrF_6AsF_6	—	(Forms HF, HBr and As compounds)	BrF_5 F_2 AsF_5	.4 .2 <.1	Strong irritant; toxic Reacts to form HF Cumulative poison (chron: systemic)
18	$NOAsF_6$	(None)	(Forms HF, and hazardous As compounds)	NOF AsF_5	— .1	Reacts to form HF Cumulative poison (chron: systemic)
19	NF_4SbF_6	None	Forms HF and poisonous Sb compounds	NF_3 F_2 SbF_5	29 .2 .5	Mildly toxic Reacts to form HF Cumulative poison (chron systemic)
20	$N_2F_3AsF_6$	—	(Forms HF and poisonous As compounds)	N_2F_4 AsF_5 F_2	— <.1 .2	More toxic than NF_3; reacts to form HF with H_2O Cumulative poison (chron systemic) Reacts to form HF
21	$RbBrF_6$	None	Forms HF and HBr	RbF BrF_3	2.5 .4	Irritant Strong irritant; toxic

70 a

ty   Decomposition Product Toxicity

Comments	Compound	Threshold Limit Value	Comments	
cts to form HF	F_2	.2	Forms HF in moist air	
t causes nervous	N_2, O_2	N/A	—	
tem disorders	MnF_2	6 ⎤	Dust causes nervous system	
	MnF_3	6 ⎦	disorders	
t-irritant	KF	2.5	Dust-irritant	
rong irritant, toxic	BrF	(.2)	Forms HF and HBr in moist air	
	F_2	.2	Forms HF in moist air	
hly toxic	NF_3	29	Mildly toxic	
50 = 200 to 500 ppm	O_2	N/A	—	(X)
ulative poison (chronic temic)	SbF_5	.5	Cumulative poison (chronic systemic)	
cts to form HF	N_2, O_2	N/A	—	
rong irritant, toxic	BrF	(.2)	Forms HF and HBr in moist air	
	F_2	.2	Forms HF in moist air	
ic, irritant	Xe	N/A	Asphyxiant	X
ic, irritant	F_2	.2	Forms HF in moist air	
ong irritant; toxic	F_2	.2	Forms HF in moist air	
	BrF	(.2)	Forms HBr and HF in moist air	X
cts to form HF				
ulative poison (chronic temic)	AsF_3	<.1	Cumulative poison (chronic systemic)	
cts to form HF	F_2	.2	Forms HF in moist air	X
ulative poison (chronic temic)	AsF_3	.1	Cumulative poison (chronic systemic)	
dly toxic	NF_3	29	Mildly toxic	
cts to form HF	F_2	.2	Forms HF in moist air	
ulative poison (chronic temic)	SbF_3	.5 ⎤	Cumulative poison (chronic systemic)	
	SbF_5	.5 ⎦		
e toxic than NF_3;	NF_3	29	Mildly toxic	
cts to form HF with	F_2	.2	Forms HF in moist air	X
	AsF_3	<.1 ⎤	Cumulative poison (chronic	
ulative poison (chronic temic)	AsF_5	<.1 ⎦	systemic)	
cts to form HF				
itant	RbF	2.5	Irritant	
ong irritant; toxic	BrF	(.2)	Forms HF and HBr in moist air	
	F_2	.2	Forms HF in moist air	

b

Reactant No.	Reactant Composition	Reactivity with		Precursor Toxicity		
		Dry Air	Moist Air	Compound	Threshold Limit Value	Comments
22	$KClF_4$	None	Forms HF and HCl	KF	2.5	Irritant
				ClF_3	.4	Strong irritant;
23	ClF_2BF_4	—	(Forms HF and HCl)	ClF_3	.4	Strong irritant;
				BF_3	3	Irritant
24	$ClF_3O \cdot BF_3$	—	Forms HF and HCl	BF_3	3	Irritant
				ClF_3O	—	(Probably similar ClF_3)
25	$CsBrF_6$	None	Forms HF and HBr	CsF	2.5	Irritant
				BrF_5	.4	Strong irritant;
26	XeF_2	None	Forms HF	XeF_2	—	Toxic; irritant
27	$NOVF_6$	None	Forms HF, NOX and V compounds	NOF	—	Reacts to forms
				VF_5	.5	Strong irritant;
28	$XeF_2 \cdot MnF_4$	(None)	(Forms HF)	XeF_2	—	Toxic; irritant
				MnF_4	6	Dust causes nerve system disorders
29	$XeF_2 \cdot VF_5$	—	(Forms HF and V compounds)	XeF_2	—	Toxic; irritant
				VF_5	.5	Strong irritant;
30	MnF_4	None	Forms HF and Mn compounds	MnF_4	6	Dust causes nerve system disorders
31	$LiMnF_5$	(None)	Forms HF	LiF	2.5	Irritant
				MnF_4	6	Dust causes nerve system disorders
32	$KMnF_5$	None	Forms HF	KF	2.5	Irritant
				MnF_4	6	Dust causes nerve system disorders

a

NOTE: Estimated quantities are in parentheses.

or Toxicity		Decomposition Product Toxicity		
Threshold Limit Value	Comments	Compound	Threshold Limit Value	Comments
5	Irritant	KF	2.5	Irritant
	Strong irritant; toxic	ClF	(.2)	Irritant; forms HF and HCl
		F_2	.2	Forms HF in moist air
	Strong irritant; toxic	BF_3	3	Irritant
		F_2	.2	Forms HF in moist air
	Irritant	ClF	.4	Forms HF and HCl in moist air
	Irritant	BF_3	3	Irritant
	(Probably similar to ClF_3)	ClF	(.2)	Forms HF and HCl in moist air
		F_2	.2	Forms HF in moist air
		O_2	N/A	—
5	Irritant	CsF	2.5	Irritant
	Strong irritant; toxic	F_2	.2	Forms HF in moist air
		BrF	(.2)	Forms HF and HBr in moist
		BrF_3	(.2)	air
	Toxic; irritant	Xe	N/A	Asphyxiant
		F_2	.2	Forms HF in moist air
	Reacts to forms HF	N_2, O_2	N/A	—
		F_2	.2	Forms HF in moist air
	Strong irritant; toxic	VF_3	.5	Forms HF and V dust —
		VF_5	.5	respiratory irritant
	Toxic; irritant	Xe	N/A	Asphyxiant
	Dust causes nervous system disorders	F_2	.2	Forms HF in moist air
		MnF_2	6	Dust causes nervous system
		MnF_3	6	disorders
	Toxic; irritant	Xe	N/A	Asphyxiant
	Strong irritant; toxic	F_2	.2	Forms HF in moist air
		VF_3	.5	Forms HF and V compounds
		VF_5	.5	in moist air
	Dust causes nervous system disorders	F_2	.2	Forms HF in moist air
		MnF_2	6	Dust causes nervous system
		MnF_3	6	disorders
	Irritant	LiF	2.5	Irritant
	Dust causes nervous system disorders	F_2	.2	Forms HF in moist air
		MnF_2	6	Dust causes nervous system
		MnF_3	6	disorders
	Irritant	KF	2.5	Irritant
	Dust causes nervous system disorders	F_2	.2	Forms HF in moist air
		MnF_2	6	Dust causes nervous system
		MnF_3	6	disorders

TABLE A-5. COMPARISON OF THEORETICAL CALCULATION RESULTS (RCL-5)

Reactant	Fuel	Reactant Weight Percent	Flame Temperature, (K)	Weight Percent F, (F, F_2, NF_3)	Primary Gas Products
$(NO)_2MnF_6$	Si_3N_4	93.0	1177	5.41	N_2, NOF, O_2, SiF_4, F_2
$KBrF_6$	Si_3N_4	96.0	1015	2.36	BrF_3, BrF_5, SiF_4, N_2, F_2
$NF_3 \cdot SbF_5$	Si_3N_4	95.0	1098	5.94	SbF_5, NOF, F_2, N_2, SiF_4, O_2
$NOBrF_4$	Si_3N_4	95.0	1164	1.37	BrF_3, N_2, O_2, NOF, SiF_4, F_2
NF_4SbF_6	Si_3N_4	95.0	1090	19.58	F_2, SbF_5, SiF_4, N_2
$RbBrF_6$	Si_3N_4	96.0	1048	2.36	BrF_3, BrF_5, SiF_4, F_2, N_2
$KClF_4$	Si_3N_4	95.0	973	11.61	ClF, F_2, SiF_4, ClF_3, N_2
$ClF_3O \cdot BF_3$	Si_3N_4	95.0	1047	7.73	BF_3, ClF, O_2, NOF, SiF_4
$CsBrF_6$	Si_3N_4	96.0	1112	2.84	BrF_3, SiF_4, F_2, N_2, BrF_5
XeF_2	Si_3N_4	96.0	1018	15.05	Xe, F_2, SiF_4, N_2
$LiMnF_5$	Mg_3N_2	99.0	921	10.86	F_2, $N_2 = 10^{-5}$

72

APPENDIX B

THEORETICAL ANALYSIS OF REACTANT SYSTEM

The theoretical combustion parameters of candidate reactant systems were calculated using current JANNAF thermodynamic product data and heats of formation of reactants, where available. Chemical equilibrium was assumed throughout the calculations. An arbitrary chamber pressure of 100 psia was chosen for this analysis. The reactant systems included in the following tables are listed in the order of the experimental evaluation, as follows:

System No.	Reactant	Fuel	Table
2324	$NOBrF_4$	Mg_3N_2	B-1
2314	$NOBrF_4$	Si_3N_4	B-2
2018	$NOBrF_4$	$(C_2F_4)_n$	B-3
2311	$(NO)_2MnF_6$	Si_3N_4	B-4
2335	$(NO)_2MnF_6$	$(C_2F_4)_n$	B-5
2325	$(NO)_2MnF_6$	Mg_3N_2	B-6
2316	$KBrF_6$	Si_3N_4	B-7
2334	$KBrF_6$	$(C_2F_4)_n$	B-8
2326	$KBrF_6$	Mg_3N_2	B-9
2343	$KBrF_6/KF$	Mg_3N_2	B-10
2317	$KClF_4$	Si_3N_4	B-11
2333	$KClF_4$	$(C_2F_4)_n$	B-12
2349	$KClF_4$	NaN_3	B-13
2327	$KClF_4$	Mg_3N_2	B-14
2342	$KClF_4/KF$	Mg_3N_2	B-15
2354	$KClF_4$	AlN	B-16
2359	$KClF_4$	Al	B-17
2321	$LiMnF_5$	Si_3N_4	B-18
2336	$LiMnF_5$	$(C_2F_4)_n$	B-19
2350	$LiMnF_5$	NaN_3	B-20
2355	$LiMnF_5$	AlN	B-21
2361	$LiMnF_5$	Al	B-22
2385	$LiMnF_5$	Mg	B-23
2372	$LiMnF_5$	Mg_3N_2	B-24
2344	$KMnF_5$	Mg_3N_2	B-25

73

System No. 2324	3	4	5	6	7	8	9	1
$NOBrF_4$, weight percent	97.00	96.00	95.00	94.00	93.00	92.00	91.00	90
Mg_3N_2, weight percent	3.00	4.00	5.00	6.00	7.00	8.00	9.00	10
Combustion parameters								
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	10
T_c K	751	1020	1181	1280	1352	1411	1469	15
γ	1.123	1.103	1.088	1.084	1.084	1.087	1.092	1
Moles gas/100 g	1.072	1.087	1.153	1.241	1.338	1.439	1.541	1
Combustion products, moles/100 g								
F	—	.0049	.0394	.1005	.1786	.2691	.3706	.4
F_2	—	.0097	.0422	.0692	.0891	.1007	.1022	.0
Br	—	—	—	—	—	—	.0002	.0
Br_2	—	—	—	—	—	—	—	
BrF	.0010	.0084	.0434	.1108	.1895	.2692	.3450	.4
BrF_3	.4283	.4698	.4568	.3909	.3091	.2249	.1440	.0
BrF_5	.0924	.0381	.0108	.0038	.0016	.0006	.0002	
MgF_2	—	—	—	—	—	—	—	
NF_3	—	.0007	.0008	.0006	.0005	.0003	.0002	.0
NO	—	—	—	.0002	.0003	.0005	.0007	.0
N_2	.2104	.2011	.2281	.2508	.2683	.2839	.2990	.3
NOF	.1575	.1921	.1526	.1218	.1014	.0847	.0688	.0
NO_2F	.0029	.0005	.0002	.0001	—	—	—	
O_2	.1792	.1615	.1788	.1915	.1990	.2045	.2097	.2
$MgF_2(1)$	—	—	—	—	—	—	—	.0
$MgF_2(s)$	.0892	.1189	.1486	.1783	.2080	.2377	.2674	.2
F, F_2, NF_3, weight percent	.00	.50	2.40	4.58	6.81	8.96	10.93	12

THEORETICAL ANALYSIS OF $NOBrF_4/Mg_3N_2$

	7	8	9	10	11	12	13	14	15
00	93.00	92.00	91.00	90.00	89.00	88.00	87.00	86.00	85.00
00	7.00	8.00	9.00	10.00	11.00	12.00	13.00	14.00	15.00
.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
0	1352	1411	1469	1536	1571	1700	1913	2083	2199
84	1.084	1.087	1.092	1.000	1.107	1.136	1.134	1.110	1.101
41	1.338	1.439	1.541	1.638	1.644	1.699	1.700	1.696	1.705
05	.1786	.2691	.3706	.4810	.5037	.5961	.6216	.6134	.6042
92	.0891	.1007	.1022	.0899	.0734	.0378	.0110	.0045	.0026
	—	—	.0002	.0004	.0007	.0028	.0198	.0663	.0137
	—	—	—	—	—	—	.0005	.0022	.0041
08	.1895	.2692	.3450	.4111	.4333	.4625	.4465	.3917	.3252
09	.3091	.2249	.1440	.0725	.0447	.0079	.0005	.0001	—
38	.0016	.0006	.0002	—	—	—	—	—	—
	—	—	—	—	—	.0003	.0035	.0159	.0387
06	.0005	.0003	.0002	.0001	—	—	—	—	—
02	.0003	.0005	.0007	.0010	.0012	.0021	.0044	.0071	.0094
08	.2683	.2839	.2990	.3147	.3264	.3437	.3569	.3647	.3714
18	.1014	.0847	.0688	.0516	.0425	.0215	.0071	.0033	.0021
01	—	—	—	—	—	—	—	—	—
15	.1990	.2045	.2097	.2154	.2172	.2246	.2279	.2257	.2232
	—	—	—	.0033	.3268	.3563	.3828	.4001	.4070
83	.2080	.2377	.2674	.2938	—	—	—	—	—
58	.81	8.96	10.93	12.56	12.36	12.76	12.23	11.83	11.58

b

TABLE B-2. THEORETICAL ANALYSIS OF $NOBrF_4/Si_3N_4$

System No. 2314	6	1	5	7	8	2	9	10	1	3
$NOBrF_4$, weight percent	96.00	95.00	93.00	92.00	91.00	90.00	89.00	88.00	87.00	85.00
Si_3N_4, weight percent	4.00	5.00	7.00	8.00	9.00	10.00	11.00	12.00	13.00	15.00
Combustion parameters										
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	977	1165	1346	1411	1482	1588	1833	2067	2227	2569
γ	1.129	1.097	1.089	1.093	1.103	1.133	1.173	1.132	1.127	1.155
Moles gas/100 g	1.179	1.249	1.465	1.583	1.700	1.803	1.840	1.848	1.872	1.907
Combustion products, moles/100 g										
F	.0017	.0265	.1519	.2368	.3331	.4347	.4811	.4736	.4771	.4613
F_2	.0024	.0223	.0628	.0711	.0670	.0435	.0096	.0027	.0013	.0004
Br	–	–	–	.0001	.0003	.0011	.0141	.0818	.1764	.3617
Br_2	–	–	–	–	–	–	.0004	.0034	.0066	.0063
BrF	.0137	.0655	.2345	.3216	.4013	.4610	.4530	.3847	.2783	.0829
BrF_3	.4812	.4391	.2648	.1728	.0878	.0220	.0007	–	–	–
BrF_5	.0215	.0063	.0009	.0003	.0001	–	–	–	–	–
NF_3	.0002	.0004	.0003	.0002	.0001	–	–	–	–	–
NO	–	.0001	.0004	.0005	.0008	.0014	.0037	.0073	.0107	.0203
NO_2F	.0005	.0002	–	–	–	–	–	–	–	–
N_2	.2394	.2619	.3045	.3243	.3449	.3679	.3903	.4028	.4132	.4320
NOF	.1509	.1291	.0901	.0736	.0554	.0320	.0081	.0027	.0014	.0005
O_2	.1822	.1906	.2047	.2101	.2164	.2251	.2333	.2314	.2273	.2156
SiF_4	.0855	.1069	.1497	.1711	.1925	.2138	.2352	.2566	.2780	.3207
F, F_2, NF_3, weight percent	.12	1.37	5.29	7.21	8.88	9.91	9.51	9.10	9.11	8.78

TABLE B-3. THEORETICAL ANALYSIS OF NOBrF$_4$/(C$_2$F$_4$)$_n$

System No. 2081	10	11	12	13	14	15	16	17
NOBrF$_4$, weight percent	60.00	65.00	70.00	75.00	80.00	85.00	87.50	90.00
(C$_2$F$_4$)$_n$, weight percent	40.00	35.00	30.00	25.00	20.00	15.00	12.50	10.00
Combustion parameters								
Pc, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
Tc, K	2199	2023	1907	1622	1352	1169	1012	798
γ	1.103	1.086	1.086	1.138	1.093	1.102	1.125	1.135
Moles gas/100 g	1.463	1.472	1.467	1.499	1.392	1.241	1.194	1.168
Combustion products, moles/100 g								
F	.1851	.1917	.1623	.1853	.1031	.0175	.0016	--
F$_2$	.0003	.0307	.0009	.0073	.0283	.0092	.0011	--
Br	.1584	.0784	.0450	.0028	--	--	--	--
Br$_2$	.0079	.0650	.0035	.0001	--	--	--	--
BrF	.1485	.2610	.3244	.3975	.2881	.1265	.0575	.0094
BrF$_3$	--	--	--	.0028	.1419	.3288	.4090	.460
BrF$_5$	--	--	--	--	.0002	.0019	.0041	.0140
CF$_4$	.5030	.4870	.5111	.4994	.3999	.2999	.2500	.2000
CO	.0018	--	--	--	--	--	--	--
COF$_2$	.2721	.1976	.0856	.0005	--	--	--	--
CO$_2$	.0229	.0151	.0031	--	--	--	--	--
NF$_3$	--	--	--	--	.0003	.0001	--	--
NO	.0004	.0022	.0025	.0011	.0003	--	--	--
N$_2$	.1611	.1734	.1864	.1967	.1918	.1933	.1985	.2046
NOF	--	.0005	.0013	.0088	.0463	.0703	.0733	.0739
O$_2$	.0012	.0594	.1404	.1964	.1917	.1932	.1984	.2041
F, F$_2$, NF$_3$, weight percent	3.53	3.67	3.12	3.80	3.03	.68	.07	.00

TABLE B-4. THEORETICAL ANALYSIS OF $(NO)_2MnF_6/Si_3N_4$

System No. 2311	4	3	2	5	1	6
$(NO)_2MnF_6$, weight percent	80.00	85.00	90.00	93.00	95.00	96.00
Si_3N_4, weight percent	20.00	15.00	10.00	7.00	5.00	4.00
Combustion parameters						
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	2853	2207	1477	1177	891	692
γ	1.093	1.113	1.094	1.086	1.080	1.084
Moles gas/100 g	1.564	1.654	1.435	1.233	1.056	1.001
Combustion products, moles/100 g						
F	.0135	.0068	.1975	.0627	.0021	-
F_2	-	-	.0291	.1049	.0303	.0016
MnF_2	.1970	.1747	-	-	-	-
MnF_3	.0109	.1952	.0608	.0006	-	-
MnF_4	-	-	.0047	.0014	-	-
NF_3	-	-	-	.0040	-	-
N_2	.6149	.5775	.5035	.3371	.0330	.0461
NOF	-	-	.0630	.3331	.1421	.0663
O_2	.2438	.3632	.3607	.2388	.6524	.7634
NO	.0392	.0153	.0012	.0001	.0858	.0272
SiF_3	.0229	-	-	-	-	-
SiF_4	.3895	.3207	.2138	.1497	.1069	.0855
$SiOF_2$	.0159	-	-	-	-	-
MnO (1)	.1404	.1440	-	-	-	-
$MnF_2(1)$	-	-	.3276	-	-	-
$MnF_3(1)$	-	-	-	-	-	-
$MnF_3(s)$	-	-	-	.4042	.4149	.4193
F, F_2, NF_3, weight percent	.26	.12	4.86	5.41	3.18	2.69

TABLE B-5. THEORETICAL ANALYSIS OF $(NO)_2MnF_6/(C_2F_4)_n$

System No. 2335	1	2	3	4	5	6	7
$(NO)_2MnF_6$, weight percent	60.00	65.00	70.00	75.00	80.00	85.00	90.00
$(C_2F_4)_n$, weight percent	40.00	35.00	30.00	25.00	20.00	15.00	10.00
Combustion parameters							
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	1745	1626	1569	1483	1251	958	599
γ	1.103	1.089	1.086	1.082	1.085	1.081	1.082
Moles gas/100 g	1.395	1.354	1.272	1.210	1.19C	1.075	.983
Combustion products, moles/100 g							
F	.162	.0077	.0060	.0072	.0558	.0042	-
F_2	-	-	-	-	.0318	.0255	.0001
CF_4	.4426	.4558	.4674	.4869	.3999	.2999	.2000
COF_2	.3001	.2102	.1203	.1286	-	-	-
CO_2	.0572	.0339	.0122	.0002	-	-	-
MnF_2	.0010	.0004	.0001	-	-	-	-
MnF_3	.2609	.2167	.1266	.0548	.0023	-	-
MnF_4	.0001	.0001	.0001	.0002	.0014	-	-
NO	.0011	.0012	.0012	.0010	.0002	-	-
ONF	.0002	.0004	.0007	.0019	.1264	.4344	.6883
N_2	.2614	.2831	.3048	.3261	.2859	.1495	.0247
NF_3	-	-	-	-	.0003	.0075	.0210
O_2	.0542	.1441	.2325	.3195	.2859	.1524	.0214
$MnF_3(1)$	-	.0667	.1789	.2726	.3456	.3712	.3931
$MnF_3(s)$	-	-	-	-	-	-	-
F, F_2, NF_3, weight percent	.31	.15	.11	.14	2.28	1.48	1.20

79

TABLE B-6. THEORETICAL ANALYSIS OF $(NO)_2MnF_6/Mg_3N_2$

System No. 2325

	3	4	5	6	7	8	9	10
$(NO)_2MnF_6$, weight percent	97.00	96.00	95.00	94.00	93.00	92.00	91.00	93.00
Mg_3N_2, weight percent	3.00	4.00	5.00	6.00	7.00	8.00	9.00	10.00
Combustion parameters								
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	474	709	897	1039	1163	1276	1350	1424
γ	1.079	1.075	1.072	1.075	1.079	1.081	1.000	1.087
Moles gas/100 g	.895	.918	.960	1.032	1.111	1.189	1.234	1.278
Combustion products, moles/100 g								
F	-	-	.0028	.0200	.0657	.1431	.2034	.2603
F_2	-	.0039	.0504	.1195	.1575	.1547	.1275	.0938
NF_3	.1048	.0822	.0579	.0248	.0086	.0027	.0011	.0004
NOF_3	.0011	.0003	.0001	-	-	-	-	-
NO_2F	.0691	.0965	.0028	.0013	.0007	.0003	.0002	.0001
N_2	.0130	.0353	.1005	.1870	.2740	.3470	.3912	.4273
ONF	.7058	.7550	.6671	.5398	.3936	.2648	.1891	.1284
O_2	.0011	.0320	.0785	.1392	.2084	.2687	.3021	.3280
MnF_3	-	-	-	-	.0004	.0036	.0125	.0312
MnF_4	-	-	-	.0003	.0014	.0037	.0060	.0069
$MgF_2(s)$	.0891	.1189	.1486	.1783	.2080	.2377	.2675	.2972
$MnF_3(l)$	-	-	-	-	-	-	.1815	.3550
$MnF_3(s)$	.4237	.4193	.4149	.4103	.4044	.3944	.1970	-
F, F_2, NF_3, weight percent	5.97	4.84	5.27	6.34	7.72	8.75	8.77	8.53

80

TABLE 3-7. THEORETICAL ANALYSIS OF KBrF$_6$/Si$_3$N$_4$

System No. 2316

	6	1	5	8	7	2	9	10	11	3
KBrF$_6$, weight percent	96.00	95.00	93.00	92.00	91.00	90.00	89.00	88.00	87.00	85.00
Si$_3$N$_4$, weight percent	4.00	5.00	7.00	8.00	9.00	10.00	11.00	12.00	13.00	15.00
Combustion parameters										
P$_c$, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T$_c$, K	1015	1126	1318	1395	1460	1530	1629	1753	1860	2252
γ	1.058	1.067	1.073	1.077	1.082	1.090	1.102	1.110	1.136	1.126
Moles gas/100 g	.613	.724	.883	.997	1.117	1.235	1.341	1.436	1.541	1.598
Combustion products, moles/100 g										
F	.0077	.0324	.1294	.2088	.2963	.3870	.4578	.4486	.3840	.3513
F$_2$	.0465	.1030	.1030	.1036	.0985	.0810	.0474	.0178	.0063	.0008
Br	-	-	-	-	.0001	.0003	.0010	.0044	.0146	.1627
Br$_2$	-	-	-	-	-	-	-	.0001	.0005	.0058
BrF	.0004	.0031	.0732	.1571	.2415	.3156	.3632	.3708	.3574	.1893
BrF$_3$	.2323	.3349	.3217	.2365	.1486	.0703	.0177	.2366	.0003	-
BrF$_5$	.1793	.0597	.0042	.0012	.0004	.0001	-	-	-	-
KF	-	-	-	.0035	.0081	.0181	-	-	-	-
K$_2$F$_2$	-	-	.0012	.0013	.0028	.0060	.0470	.1290	.2549	.3414
KBr	-	-	.0004	-	-	-	.0144	.0358	.0592	.0114
NF$_3$	.0078	.0054	.0007	.0004	.0002	.0001	-	-	-	.0011
N$_2$	.0531	.0686	.0994	.1139	.1282	.1425	.1568	.1711	.1853	.2138
SiF$_4$	.0855	.1069	.1497	.1711	.1925	.2139	.2352	.2566	.2780	.3208
KF(1)	-	-	-	-	-	-	-	-	-	-
KF(s)	.4120	.4076	.3970	.3888	.3768	.3561	.3061	.1772	-	-
F, F$_2$, NF$_3$, weight percent	2.36	4.85	6.41	7.93	9.38	10.43	10.50	9.20	7.53	6.68

TABLE B-8. THEORETICAL ANALYSIS OF KBrF$_6$/(C$_2$F$_4$)$_n$

System No. 2334

	2	3	4	5	6	7
KBrF$_6$, weight percent	65.00	70.00	75.00	80.00	85.00	90.00
(C$_2$F$_4$)$_n$, weight percent	35.00	30.00	25.00	20.00	15.00	10.00
Combustion parameters						
P$_c$, psia	100.0	100.0	100.0	100.0	100.0	100.0
T$_c$, K	2025	1817	1521	1342	1131	919
γ	1.110	1.097	1.087	1.072	1.000	1.059
Moles gas/100 g	1.186	1.145	1.053	.882	.725	.594
Combustion products, moles/100 g						
F	.0049	.0517	.1884	.0945	.0209	.0010
F$_2$	-	.0002	.0244	.0423	.0393	.0065
Br	.1733	.0379	.0004	-	-	-
BrF	.0179	.2505	.2960	.1469	.0903	.0002
BrF$_3$	-	-	.0255	.1956	.3316	.2064
BrF$_5$	-	-	.0001	.0008	.0242	.1796
Br$_2$	.0301	.0059	-	-	-	-
CF$_4$	.6996	.5999	.4999	.3999	.2999	.2000
KBr	.0270	.0602	-	-	-	-
KF	.2135	.1575	.0141	.0016	-	-
K$_2$F$_2$	.0190	.0414	.0047	.0006	-	-
KF(l)	-	.0598	.2983	.3405	.3363	.3863
KF(s)	-	-	-	-	.0284	-
F, F$_2$, NF$_3$, weight percent	.09	.99	4.51	3.40	1.89	.27

System No. 2326	3	4	5	6	7	8	9	10
$KBrF_6$, weight percent	97.00	96.00	95.00	94.00	93.00	92.00	91.00	90.
Mg_3N_2, weight percent	3.00	4.00	5.00	6.00	7.00	8.00	9.00	10.
Combustion parameters								
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	10
T_c, K	891	1029	1128	1195	1311	1392	1455	15
γ	1.047	1.055	1.062	1.065	1.069	1.073	1.077	1.
Moles gas/100 g	.458	.536	.634	.681	.763	.856	.957	1.
Combustion products, moles/100 g								
F	.0007	.0100	.0356	.0635	.1400	.2290	.3243	.4
F_2	.0086	.0687	.1372	.1521	.1524	.1486	.1443	.1
BrF	—	.0003	.0020	.0070	.0419	.1095	.1847	.2
BrF_3	.1055	.2074	.3109	.3547	.3487	.2829	.2050	.1
BrF_5	.3108	.2042	.0948	.0418	.0086	.0025	.0009	.0
N_2	.0272	.0344	.0458	.0573	.0687	.0789	.0890	.0
NF_3	.0050	.0103	.0075	.0043	.0013	.0006	.0004	.0
KF	—	—	—	.0001	.0009	.0029	.0065	.0
K_2F_2	—	—	—	—	.0004	.0011	.0023	.0
KF(l)	—	—	—	.4032	.3975	.3898	.3794	.3
KF(s)	.4163	.4120	.4076	—	—	—	—	
MgF_2(l)	—	—	—	—	—	—	—	
MgF_2(s)	.0891	.1189	.1486	.1783	.2080	.2377	.2675	.2
F, F_2, NF_3, weight percent	.62	3.39	6.32	7.23	8.55	10.03	11.66	13

G.

7	8	9	10	11	12	13	14	15
93.00	92.00	91.00	90.00	89.00	88.00	87.00	86.00	85.00
7.00	8.00	9.00	10.00	11.00	12.00	13.00	14.00	15.00
100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
1311	1392	1455	1513	1537	1605	1693	1788	1881
1.069	1.073	1.077	1.081	1.083	1.089	1.097	1.102	1.115
.763	.856	.957	1.061	1.075	1.162	1.240	1.314	1.389
.1400	.2290	.3243	.4254	.4453	.5331	.5906	.5892	.5522
.1524	.1486	.1443	.1325	.1163	.0889	.0533	.0268	.0127
.0419	.1095	.1847	.2565	.2839	.3337	.3593	.3618	.3527
.3487	.2829	.2050	.1294	.0977	.0434	.0125	.0029	.0007
.0086	.0025	.0009	.0003	.0001	—	—	—	—
.0687	.0789	.0890	.0990	.1089	.1188	.1288	.1387	.1486
.0013	.0006	.0004	.0002	.0001	—	—	—	—
.0009	.0029	.0065	.0131	.0168	.0334	.0724	.1496	.2526
.0004	.0011	.0023	.0044	.0055	.0104	.0211	.0403	.0561
.3975	.3898	.3794	.3643	.3541	.3234	.2589	.1388	—
—	—	—	—	—	—	—	—	—
—	—	—	—	.3269	.3566	.3861	.4153	.4437
.2080	.2377	.2675	.2972	—	—	—	—	—
8.53	10.03	11.66	13.13	12.89	13.51	13.25	12.21	10.98

b

TABLE B-10. THEORETICAL ANALYSIS OF $KBrF_6-(95/5)/Mg_3N_2$

System No. 2343	13	12	11	1	2	3	4	5	6	7	8	9	10
$KBrF_6$-KF(95/5), weight percent	87.0	88.0	89.0	90.0	91.0	92.0	93.0	94.0	95.0	96.0	97.0	96.0	99.0
Mg_3N_2, weight percent	13.0	12.0	11.0	10.0	9.0	8.0	7.0	6.0	5.0	4.0	3.0	2.0	1.0
Combustion parameters													
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	1726	1629	1553	1526	1465	1402	1321	1204	1131	1038	902	642	338
γ	1.097	1.090	1.083	1.081	1.076	1.072	1.068	1.064	1.000	1.054	1.045	1.045	1.047
Moles gas/100 g	1.192	1.120	1.037	1.025	.923	.822	.730	.650	.603	.517	.439	.419	.414
Combustion products, moles/100 g													
Br	.0021	.0007	.0003	.0002	-	-	-	-	-	-	-	-	-
BrF	.3454	.3287	.2853	.2596	.1902	.1157	.0468	.0080	.0021	.0004	-	-	-
BrF_3	.0072	.0294	.0772	.1070	.1801	.2574	.3255	.3410	.3000	.2080	.1071	-	-
BrF_5	-	-	-	.0002	.0007	.0020	.0068	.0343	.0855	.1831	.2883	.0595	.0297
F	.5556	.5185	.4381	.4199	.3203	.2261	.1393	.0639	.0343	.0108	.0009	.3401	.37 9
F_2	.0392	.0726	.1024	.1192	.1326	.1372	.1398	.1413	.1278	.0699	.0099	-	-
KF	.0886	.0393	.0187	.0144	.0071	.0031	.0010	.0002	-	-	-	-	-
K_2F_2	.0251	.0121	.0061	.0048	.0025	.0011	.0004	-	-	-	-	-	-
NF_3	-	-	.0001	.0002	.0003	.0005	.0011	.0036	.0069	.0097	.0052	-	-
N_2	.1488	.1158	.1089	.0950	.0890	.0790	.0688	.0576	.0461	.0348	.0271	.0198	.0099
KF (1)	.2908	.3710	.4085	.4204	.4374	.4489	.4574	.4639	.0909	-	-	-	-
KF (~)	-	-	-	-	-	-	-	-	.3781	.4740	.4790	.4839	.4889
M_gF_2 (1)	.3860	.3563	.3269	-	-	-	-	-	-	-	-	-	-
M_gF_2 (~)	-	-	-	.2972	.2675	.2377	.2080	.1783	.1486	.1189	.0892	.0594	.0297
F, F_2, NF_3, weight percent	12.04	12.60	12.22	12.52	11.14	9.54	8.02	6.79	5.90	3.41	.69	-	-

TABLE B-11. THEORETICAL ANALYSIS OF $KClF_4/Si_3N_4$

System No. 2317	6	1	7	5	8	4	2	3
$KClF_4$, weight percent	96.00	95.00	94.00	93.00	92.00	91.00	90.00	85.00
Si_3N_4, weight percent	4.00	5.00	6.00	7.00	8.00	9.00	10.00	15.00
Combustion parameters								
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	838	973	1126	1205	1378	1554	1706	2174
γ	1.081	1.087	1.096	1.094	1.098	1.102	1.100	1.119
Moles gas/100 g	.975	1.115	1.217	1.236	1.297	1.351	1.411	1.780
Combustion products, moles/100 g								
F	.0022	.0158	.0716	.1172	.2547	.3453	.3326	.2470
F_2	.1375	.2502	.2987	.2480	.1405	.0483	.0136	.0005
Cl	-	-	-	-	.0001	.0011	.0071	.1998
ClF	.4759	.5909	.6164	.6145	.6103	.6014	.5782	.1802
ClF_3	.1618	.0401	.0080	.0031	.0005	-	-	-
Cl_2	-	-	-	-	.0001	-	-	-
KF	-	-	-	.0003	.0037	.0009	.0062	.0835
K_2F_2	-	-	-	.0001	.0014	.0247	.0507	.4878
NF_3	.1108	.0794	.0168	.0057	.0005	.0081	-	.0297
N_2	.0016	.0316	.0771	.0969	.1138	.1283	.1426	.2138
SiF_4	.0855	.1069	.1283	.1497	.1711	.1925	.2139	.3298
KCl	-	-	-	-	-	-	-	.0174
KF(l)	-	-	.6242	.6172	.6046	.5636	.4547	-
KF(s)	.6377	.6310	-	-	-	-	-	-
F, F_2, NF_3, weight percent	11.58	11.61	13.67	11.98	10.21	8.40	6.84	4.71

85

TABLE B-12. THEORETICAL ANALYSIS OF $KClF_4/(C_2F_4)_n$

System No. 2333

	2	3	4	5	6	7
$KClF_4$, weight percent	65.00	70.00	75.00	80.00	85.00	90.00
$(C_2F_4)_n$, weight percent	35.00	30.00	25.00	20.00	15.00	10.00
Combustion parameters						
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	1985	1849	1711	1351	1040	772
γ	1.103	1.097	1.087	1.090	1.096	1.673
Moles gas/100 g	1.312	1.125	1.146	1.134	1.129	.898
Combustion products, moles/100 g						
F	.0065	.0412	.0872	.1373	.0297	.0006
F_2	-	.0001	.0011	.0628	.2348	.1001
CF_4	.6979	.5998	.4999	.4000	.3000	.2000
Cl	.0958	.0582	.0162	.0001	-	-
ClF	.0124	.1605	.4055	.5301	.5496	.3005
ClF_3	-	-	-	.0002	.0150	.2973
Cl_2	.1002	.1197	.0381	.0002	-	-
KCl	.1128	.0067	.0002	.0002	-	-
KF	.2502	.2105	.0763	.0023	-	-
K_2Cl_2	.0043	-	-	-	-	-
K_2F_2	.0301	.0539	.0219	.0009	-	-
KF(l)	-	.1398	.3779	.5273	.5646	.5978
KF(ϵ)	-	-	-	-	-	-
F, F_2, NF_3, weight percent	.12	.79	1.70	4.99	9.49	3.82

86

TABLE B-13. THEORETICAL ANALYSIS OF $KClF_4/NaN_3$

System No. 2349	1	2	3	4	5	6	7	8	9	10	11
$KClF_4$, weight percent	85.0	86.0	87.0	88.0	89.0	90.0	91.0	92.0	93.0	94.0	95.0
NaN_3, weight percent	15.0	14.0	13.0	12.0	11.0	10.0	9.0	8.0	7.0	6.0	5.0
Combustion parameters											
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	997	959	920	877	828	768	695	613	530	450	371
Moles gas/100 g	1.220	1.170	1.119	1.069	1.023	.983	.948	.916	.880	.837	.790
Combustion products, moles/100 g											
ClF	.5423	.5406	.5367	.5296	.5178	.4986	.4680	.4215	.3553	.2701	.1707
ClF_3	.0223	.0306	.0412	.0549	.0734	.0992	.1365	.1896	.2625	.3542	.4603
F	.0200	.0119	.0065	.0031	.0011	.0003	–	–	–	–	–
F_2	.2262	.1817	.1348	.0895	.0494	.0202	.0050	.0006	–	–	–
NF_3	.1271	.1635	.1991	.2210	.2555	.2676	.2625	.2395	.2009	.1493	.0882
N_2	.2825	.2412	.2004	.1613	.1260	.0969	.0764	.0648	.0610	.0638	.0713
KF(s)	.5645	.5712	.5779	.5845	.5912	.5978	.6045	.6111	.6177	.6244	.6310
NaF(s)	.2307	.2153	.1999	.1846	.1692	.1538	.1384	.1230	.1077	.0923	.0769
F, F_2, NF_3, weight percent	16.22	16.45	16.59	16.62	16.46	16.02	15.15	13.68	11.45	8.51	5.02

TABLE B-14. THEORETICAL ANALYSIS OF $KClF_4/Mg_3N_2$

System No. 2327	3	4	5	6	7	8	9	10
$KClF_4$, weight percent	97.00	96.00	95.00	94.00	93.00	92.00	91.00	90.00
Mg_3N_2, weight percent	3.00	4.00	5.00	6.00	7.00	8.00	9.00	10.00
Combustion parameters								
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	715	832	958	1101	1169	1322	1464	1536
γ	1.066	1.076	1.084	1.088	1.086	1.087	1.091	1.000
Moles gas/100 g	.747	.896	1.030	1.121	1.129	1.183	1.236	1.233
Combustion products, moles/100 g								
F	.0001	.0022	.0141	.0619	.1011	.2391	.3856	.4201
F_2	.0432	.1775	.2956	.3626	.3352	.2499	.1438	.0911
ClF	.2217	.4156	.5703	.6109	.6133	.6096	.6035	.5961
ClF_3	.4225	.2220	.0607	.0134	.0064	.0013	.0003	.0001
ClF_5	.0001	-	-	-	-	-	-	-
NF_3	.0594	.0788	.0794	.0260	.0118	.0017	.0002	.0001
N_2	-	.0002	.0098	.0464	.0634	.0784	.0890	.0990
Cl	-	-	-	-	-	-	-	.0007
Cl_2	-	-	-	-	-	-	-	.0004
KF	-	-	-	-	.0001	.0017	.0094	.0151
K_2F_2	-	-	-	-	-	.0006	.0033	.0063
KF(1)	.6443	.6377	.6310	.6243	.6174	.6081	.5884	.5661
KF(s)	-	-	-	-	-	-	-	-
MgF_2(1)	-	-	-	-	-	-	-	.2838
MgF_2(s)	.0892	.1189	.1486	.1783	.2080	.2377	.2684	.0134
F, F_2, NF_3, weight percent	5.03	11.27	16.03	16.44	15.33	14.14	12.81	11.44

TABLE B-15. THEORETICAL ANALYSIS OF KClF$_4$-KF(95/5)/Mg$_3$N$_2$

System No. 2342	10	9	8	7	6	1	2	3	4
KClF$_4$-KF(95/5), weight percent	90.0	91.0	92.0	93.0	94.0	95.0	96.0	97.0	98.0
Mg$_3$N$_2$, weight percent	10.0	9.0	8.0	7.0	6.0	5.0	4.0	3.0	2.0
Combustion parameters									
P$_c$, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T$_c$, K	1562	1492	1345	1191	1129	980	847	729	509
γ	1.089	1.089	1.085	1.083	1.086	1.082	1.076	1.065	1.065
Moles gas/100 g	1.170	1.177	1.127	1.077	1.077	.994	.871	.723	.658
Combustion products, moles/100 g									
Cl	.0009	.0004	-	-	-	-	-	-	-
ClF	.5658	.5732	.5794	.5821	.5837	.5543	.4215	.2296	.1189
ClF$_3$	-	.0002	.0010	.0048	.0095	.0452	.1843	.3824	.4995
ClF$_5$	-	-	-	-	-	-	-	.0001	-
Cl$_2$	.0006	.0003	-	-	-	-	-	-	-
F	.4020	.3821	.2477	.1104	.0736	.0173	.0027	.0002	-
F$_2$	.0706	.1157	.2162	.3061	.3413	.2931	.1836	.0512	-
KF	.0231	.0117	.0022	.0002	-	-	-	-	-
K$_2$F$_2$	.0075	.0041	.0008	-	-	-	-	-	-
NF$_3$	-	.0002	.0012	.0085	.0182	.0693	.0785	.0594	.0396
N$_2$	.0990	.0891	.0786	.0651	.0503	.0149	.0004	-	-
KF (l)	.6073	.6326	.6559	.6665	.6739	.6812	.6884	.6956	.7027
KF (s)	-	-	-	-	-	-	-	-	-
MgF$_2$ (l)	.2971	-	-	-	-	-	-	-	-
MgF$_2$ (s)	-	.2675	.2377	.2080	.1783	.1486	.1189	.0892	.0594
F, F$_2$, NF$_3$, weight percent	10.32	11.67	12.99	14.21	15.40	15.42	11.50	5.33	2.26

TABLE B-16. THEORETICAL ANALYSIS OF KClF$_4$/AlN

System No. 2354	1	2	3	4	5	6	7	8	9
KClF$_4$, weight percent	90.0	91.0	92.0	93.0	94.0	95.0	96.0	97.0	98.0
AlN, weight percent	10.0	9.0	8.0	7.0	6.0	5.0	4.0	3.0	2.0
Combustion parameters									
P$_c$, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T$_c$, K	1785	1680	1510	1343	1163	1024	878	751	531
γ	1.079	1.087	1.094	1.089	1.087	1.085	1.080	1.068	1.070
Moles gas/100 g	1.297	1.272	1.256	1.195	1.131	1.070	.949	.787	.700
Combustion products, moles/100 g									
AlF$_3$	.0620	.0237	—	—	—	—	—	—	—
Al$_2$F$_6$	.0004	.0001	—	—	—	—	—	—	—
Cl	.0106	.0034	.0005	.0001	—	—	—	—	—
ClF	.5733	.5968	.6098	.6165	.6177	.6022	.5007	.2886	.1464
ClF$_3$	—	—	.0002	.0011	.0067	.0288	.1370	.3557	.5045
ClF$_5$	—	—	—	—	—	—	—	.0001	—
Cl$_2$	.0069	.0021	.0003	.0001	—	—	—	—	—
F	.4553	.4818	.4176	.2584	.0964	.0290	.0045	.0004	—
F$_2$	.0165	.0380	.1097	.2294	.3310	.3213	.2206	.0689	—
KF	.0461	.0155	.0153	.0022	.0001	—	—	—	.0001
K$_2$F$_2$	.0040	.0011	.0051	.0008	.0001	—	—	—	—
NF$_3$	—	—	—	.0013	.0126	.0556	.0043	.0731	.0487
N$_2$	.1220	.1098	.0975	.0847	.0669	.0332	.0016	—	—
KF(1)	—	—	—	.1015	.1850	.2651	.3449	.4247	.5046
KF(s)	—	—	—	—	—	—	—	—	—
K$_3$AlF$_6$(s)	.1813	.1956	.1952	.1708	.1464	.1220	.0976	.0732	.0488
F, F$_2$, NF$_3$, weight percent	9.28	10.60	12.11	13.70	15.13	15.93	13.46	6.79	2.78

TABLE B-17. THEORETICAL ANALYSIS OF $KClF_4/Al$

System No. 2359	1	2	3	4	5	6	7	8	9	10
$KClF_4$, weight percent	90.0	91.0	92.0	93.0	94.0	95.0	96.0	97.0	98.0	99.0
Al, weight percent	10.0	9.0	8.0	7.0	6.0	5.0	4.0	3.0	2.0	1.0
Combustion parameters										
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	2153	2007	1977	1933	1861	1685	1394	1104	828	525
γ	1.119	1.077	1.077	1.076	1.077	1.100	1.091	1.093	1.075	1.065
Moles gas/100 g	1.861	1.776	1.652	1.533	1.426	1.355	1.233	1.141	.902	.658
Combustion products, moles/100 g										
$AlClF_2$	.0001	—	—	—	—	—	—	—	—	—
AlF_3	.368.	.3182	.2322	.1476	.0659	.0008	—	—	—	—
Al_2F_6	.0010	.0017	.0012	.0007	.0002	—	—	—	—	—
Cl	.1715	.0856	.0618	.0391	.0190	.0032	.0001	—	—	—
ClF	.2815	.4160	.4775	.5349	.5853	.6245	.6366	.6289	.3608	.0561
ClF_3	—	—	—	—	—	—	.0008	.0154	.2901	.6014
Cl_2	.0677	.0498	.0352	.0216	.0100	.0017	.0001	—	—	—
F	.4067	.3945	.4588	.5248	.5892	.6041	.3508	.0698	.0024	—
F_2	.0013	.0026	.0044	.0078	.0158	.0542	.2392	.4272	.2484	.0003
KCl	.0093	.0031	.0014	.0005	.0001	—	—	—	—	—
KF	.5173	.4434	.3345	.2271	.1254	.0543	.0043	—	—	—
K_2F_2	.0356	.0611	.0448	.0292	.0154	.0117	.0016	—	—	—
$KF(l)$	—	—	—	—	—	—	.1855	—	—	—
$KF(s)$	—	—	—	—	—	—	—	.3106	.4286	.5464
$K_3AlF_6(s)$	—	.0119	.0619	.1106	.1560	.1845	.1483	.1112	.0741	.0371
F, F_2, NF_3, weight percent	7.78	7.59	8.88	10.27	11.79	13.54	15.75	17.56	9.48	.01

TABLE B-18. THEORETICAL ANALYSIS OF $LiMnF_5/Si_3N_4$

System No. 2321	1	2	3
$LiMnF_5$, weight percent	95.00	90.00	85.00
Si_3N_4, weight percent	5.00	10.00	15.00
Combustion parameters			
P_c psia	100.0	100.0	100.0
T_c, K	1395	1806	2067
Moles gas/100 g	.314	.682	.777
Combustion products, moles/100 g			
F	.0796	.0036	—
F_2	.0476	—	—
LiF	.0001	.0184	.1257
Li_2F_2	.0001	.0089	.0442
Li_3F_3	—	.0014	.0070
Mn	—	—	.0284
MnF_2	—	.0051	.0372
MnF_3	.0056	.2884	—
MnF_4	.0022	—	—
NF_3	.0003	· —	—
N_2	.0711	.1426	.2139
SiF_3	—	—	.0286
SiF_4	.1069	.2139	.2921
LiF (1)	.6052	.5331	.3066
Mn (1)	—	—	.0569
MnF_2 (1)	—	—	.4193
MnF_3 (1)	.5978	.2803	—
F, F_2, NF_3, weight percent	3.34	.07	—

TABLE B-19. THEORETICAL ANALYSIS OF $LiMnF_5/(C_2F_4)_n$

System No. 2336	7	8	9	10	11	12	13	14	15	16
$LiMnF_5$, weight percent	90.00	95.00	96.00	97.00	98.00	99.00	99.10	99.20	99.30	99.40
$(C_2F_4)_n$, weight percent	10.00	5.00	4.00	3.00	2.00	1.00	.90	.80	.70	.60
Combustion parameters										
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	1307	1070	996	918	837	752	744	735	726	718
γ	1.027	1.024	1.023	1.022	1.022	1.023	1.023	1.023	1.023	1.023
Moles gas/100 g	.317	.312	.311	.311	.313	.316	.316	.316	.316	.317
Combustion products, moles/100 g										
F	.0549	.0184	.0099	.0046	.0017	.0005	.0004	.0004	.0003	.0003
F_2	.0587	.1934	.2210	.2469	.2715	.2953	.2976	.3000	.3023	.3047
CF_4	.2000	.1000	.0800	.0600	.0400	.0200	.0180	.0160	.0140	.0120
MnF_3	.0016	-	-	-	-	-	-	-	-	-
MnF_4	.0016	.0003	.0001	-	-	-	-	-	-	-
$LiF(l)$	.5736	-	-	-	-	-	-	-	-	-
$LiF(s)$	-	.6056	.6120	.6183	.6247	.6311	.6317	.6324	.6330	.6336
$MnF_3(s)$	.5706	.6053	.6118	.6183	.6247	.6311	.6317	.6324	.6330	.6336
F, F_2, NF_3, weight percent	3.27	7.70	8.58	9.47	10.35	11.23	11.32	11.41	11.49	11.63

93

TABLE B-20. THEORETICAL ANALYSIS OF $LiMnF_5/NaN_3$

System No. 2350	1	2	3	4	5	6	7	8	9	10
$LiMnF_5$, weight percent	90.0	91.0	92.0	93.0	94.0	95.0	96.0	97.0	98.0	99.0
NaN_3, weight percent	10.0	9.0	8.0	7.0	6.0	5.0	4.0	3.0	2.0	1.0
Combustion parameters										
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	1207	1161	1121	1121	1111	1070	1028	982	909	791
γ	1.040	1.040	1.000	1.000	1.040	1.040	1.038	1.034	1.020	1.020
Moles gas/100 g	.459	.429	.398	.385	.367	.331	.295	.262	.254	.285
Combustion products, moles/100 g										
F	.0585	.0417	.0294	.0297	.0273	.0177	.0109	.0063	.0030	.0008
F_2	.1619	.1678	.1664	.1753	.1809	.1690	.1523	.1379	.1596	.2383
MnF_3	.0004	.0001	.0001	.0001	-	-	-	-	-	-
MnF_4	.0014	.0009	.0006	.0006	.0005	.0003	.0002	.0001	-	-
NF_3	.0121	.0211	.0335	.0348	.0391	.0575	.0783	.0967	.0906	.0461
N_2	.2247	.1971	.1678	.1441	.1188	.0866	.0532	.0208	.0009	-
LiF(l)	.5737	.5801	.5603	.2448	-	-	-	-	-	-
LiF(s)	-	-	.0261	.3481	.5992	.6056	.6120	.6183	.6247	.6311
MnF_3(s)	.5719	.5790	.5858	.5922	.5987	.6053	.6118	.6183	.6247	.6311
NaF(s)	.1538	.1384	.1230	.1077	.0923	.0769	.0615	.0461	.0308	.0154
F, F_2, NF_3, weight percent	7.95	8.37	8.79	9.21	9.62	10.04	10.45	10.87	11.2°	11.70

TABLE B-21. THEORETICAL ANALYSIS OF LiMnF$_5$/AlN

System No. 2355	1	2	3	4	5
LiMnF$_5$, weight percent	95.0	96.0	97.0	98.0	99.0
AlN, weight percent	5.0	4.0	3.0	2.0	1.0
Combustion parameters					
P$_c$, psia	100.0	100.0	100.0	100.0	100.0
T$_c$, K	1364	1350	1195	1105	930
γ	1.025	1.000	1.027	1.028	1.019
Moles gas/100 g	.221	.254	.247	.252	.269
Combustion products, moles/100 g					
F	.0736	.0868	.0398	.0223	.0048
F$_2$	.0803	.1126	.1643	.1939	.2401
LiAlF$_4$	-	.0002	-	-	-
MnF$_3$	.0027	.0026	.0002	-	-
MnF$_4$	.0022	.0026	.0009	.0004	-
NF$_3$	.0011	.0015	.0098	.0226	.0243
N$_2$	.0605	.0480	.0317	.0131	-
LiF(l)	.2398	.3194	.3988	-	-
LiF(s)	-	-	-	-	.5579
Li$_3$AlF$_6$(l)	.1218	.0974	.0732	.4783	-
Li$_3$AlF$_6$(s)	-	-	-	.0488	.0234
MnF$_3$(l)	.6007	.0079	-	-	-
MnF$_3$(s)	-	.5988	.6172	.6243	.6310
F,F$_2$,NF$_3$, weight percent	4.51	6.01	7.56	9.08	10.60

95

TABLE B-22. THEORETICAL ANALYSIS OF LiMnF$_5$/Al

System No. 2361	1	2	3	4	5
LiMnF$_5$, weight percent	95.0	96.0	97.0	98.0	99.0
Al, weight percent	5.0	4.0	3.0	2.0	1.0
Combustion parameters					
P$_c$, psia	100.0	100.0	100.0	100.C	100.0
T$_c$, K	1857	1735	1480	1328	1079
γ	1.098	1.063	1.032	1.028	1.021
Moles gas/100 g	.424	.264	.218	.249	.271
Combustion products, moles/100g					
AlF$_3$	.0036	.0008	-	-	-
F	.0488	.1431	.1275	.0891	.0210
F$_2$	.0004	.0110	.0771	.1554	.2493
LiAlF$_4$	.0211	.0065	.0007	.0001	-
LiF	.0169	.0040	.0002	-	-
Li$_2$F$_2$	.0077	.0021	.0001	-	-
Li$_3$F$_3$	.0012	.0003	-	-	-
MnF$_2$	.0005	-	-	-	-
MnF$_3$	.3236	.0945	.0096	.0018	-
MnF$_4$	.0006	.0021	.0030	.0026	.0004
LiF(1)	.0666	.1734	.2855	.4025	.5199
LiF(s)	-	-	-	-	.0371
Li3AlF$_6$(1)	.1606	.1409	.1105	.0740	-
MnF$_3$(1)	.2809	.5154	.6057	.6204	-
MnF$_3$(s)	-	-	-	-	.6307
F,F$_2$,NF$_3$, weight percent	.94	3.14	5.35	7.59	9.87

TABLE B-23. THEORETICAL ANALYSIS OF LiMnF$_5$/Mg

System No. 2385	1	2	3	4	5
LiMnF$_5$, weight percent	95.0	96.0	97.0	98.0	99.0
Mg, weight percent	5.0	4.0	3.0	2.0	1.0
Combustion parameters					
P$_c$, psia	100.0	100.0	100.0	100.0	100.0
T$_c$, K	1727	1536	1350	1219	1030
Moles gas/100 g	.282	.239	.236	.258	.282
Combustion products, moles/100 g					
F	.1635	.1537	.0926	.0530	.0144
F$_2$	.0143	.0680	.1382	.2029	.2671
LiF	.0039	.0005	—	—	—
Li$_2$F$_2$	.0021	.0004	—	—	—
Li$_3$F$_3$	—	.0001	—	—	—
MnF$_3$	.0953	.0178	.0024	.0003	—
MnF$_4$	.0024	.0033	.0027	.0013	.0002
LiF(1)	.5964	.6106	.6182	.6247	—
LiF(s)	—	—	—	—	.6311
MgF$_2$(1)	.2055	.1321	—	—	—
MgF$_2$(s)	—	.0324	.1234	.0822	.0411
MnF$_3$(1)	.5079	.5909	.5065	—	—
MnF$_3$(s)	—	—	.1066	.6231	.6309
F, F$_2$, NF$_3$, weight percent	3.65	5.31	7.01	8.72	10.42

System No. 2322	11	10	9	8	7	6	12	13	14	15
$LiMnF_5$, weight percent	99.50	99.40	99.30	99.20	99.10	99.00	98.90	98.80	98.70	98.60
Mg_3N_2, weight percent	.50	.60	.70	.80	.90	1.00	1.10	1.20	1.30	1.40
Combustion parameters										
P_c, psia	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
T_c, K	797	822	847	872	897	921	944	968	991	1012
γ	1.021	1.021	1.021	1.020	1.020	1.020	1.020	1.020	1.021	1.022
Moles gas/100 g	.298	.294	.290	.286	.282	.287	.275	.271	.268	.266
Combustion products, moles/100 g										
F	.0009	.0014	.0019	.0026	.0034	.0045	.0058	.0073	.0090	.0109
F_2	.2869	.2805	.2739	.2673	.2606	.2539	.2471	.2404	.2339	.2282
MnF_3	--	--	--	--	--	--	--	--	--	--
MnF_4	--	--	--	--	--	--	.0001	.0001	.0001	.0002
NF_3	.0099	.0119	.0139	.0159	.0178	.0198	.0217	.0235	.0250	.0260
N_2	--	--	--	--	--	--	.0001	.0002	.0004	.0009
$LiF(1)$	--	--	--	--	--	--	--	--	--	--
$LiF(s)$	.6343	.6336	.6330	.6324	.6317	.6311	.6304	.6298	.6292	.6285
$MgF_2(s)$	.0149	.0178	.0208	.0238	.0267	.0297	.0327	.0357	.0386	.0416
$MnF_3(1)$	--	--	--	--	--	--	--	--	--	--
$MnF_3(s)$	.6343	.6336	.6330	.6323	.6317	.6310	.6304	.6297	.6291	.6284
F, F_2, NF_3, weight percent	11.49	11.36	11.24	11.11	10.98	10.86	10.75	10.60	10.50	10.36

a

THEORETICAL ANALYSIS OF LiMnF$_5$/Mg$_3$N$_2$

	6	12	13	14	15	16	5	4	3	2
0	99.00	98.90	98.80	98.70	98.60	98.50	98.00	97.00	96.00	95.00
0	1.00	1.10	1.20	1.50	1.40	1.50	2.00	3.00	4.00	5.00
0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
	921	944	968	991	1012	1033	1121	1190	1347	1358
0	1.020	1.020	1.020	1.021	1.022	1.024	1.000	1.028	1.031	1.030
	.287	.275	.271	.268	.266	.265	.269	.261	.278	.250
4	.0045	.0058	.0073	.0090	.0109	.0131	.0273	.0419	.0978	.0877
6	.2539	.2471	.2404	.2339	.2282	.2234	.2119	.1834	.1343	.1070
	—	—	—	—	—	—	—	.0002	.0027	.0029
	—	.0001	.0001	.0001	.0002	.0002	.0005	.0010	.0029	.0026
8	.0198	.0217	.0235	.0250	.0260	.0262	.0181	.0101	.0017	.0013
	—	.0001	.0002	.0004	.0009	.0018	.0108	.0246	.0387	.0488
	—	—	—	—	—	—	.0103	.6183	.6118	.0054
7	.6311	.6304	.6298	.6292	.6285	.6279	.6144	—	—	—
7	.0297	.0327	.0357	.0386	.0416	.0445	.0594	.0891	.1189	.1486
	—	—	—	—	—	—	—	—	—	.6001
7	.6310	.6304	.6297	.6291	.6284	.6277	.6241	.6172	.6063	—
8	10.86	10.75	10.60	10.50	10.36	10.23	9.61	8.34	7.05	5.81

TABLE B-25. THEORETICAL ANALYSIS OF $KMnF_5/Mg_3N_2$

System No. 2344	1	2	3	4	5
$KMnF_5$, weight percent	95.0	96.0	97.0	98.0	99.0
Mg_3N_2, weight percent	5.0	4.0	3.0	2.0	1.0
Combustion parameters					
P_c, psia	100.0	100.0	100.0	100.0	100.0
T_c, K	1350	1161	1060	810	483
γ	1.000	1.024	1.027	1.015	1.021
Moles gas/100 g	.184	.175	.172	.180	.222
Combustion products, moles/100 g					
F	.0585	.0213	.0098	.0006	–
F_2	.0710	.1076	.1174	.1400	.2024
KF	.0004	–	–	–	–
K_2F_2	.0001	–	–	–	–
MnF_3	.0019	–	–	–	–
MnF_4	.0017	.0005	.0002	–	–
NF_3	.0911	.0101	.0300	.0396	.0198
N_2	.0490	.0341	.0147	–	–
KF(l)	.5019	.5078	–	–	–
KF(s)	–	–	.5131	.5184	.5237
MgF_2(s)	.1486	.1189	.0892	.0594	.0297
MnF_3(l)	.0196	–	–	–	–
MnF_3(s)	.4793	.5073	.5130	.5184	.5237
F, F_2, NF_3, weight percent	3.87	5.13	6.36	7.59	8.82

APPENDIX C

X-RAY ANALYSIS DATA FOR $LiMnF_5$ AND MnF_4

All Debye-Scherrer X-ray powder patterns were taken using a 57.3-mm-diameter camera with $CuK\alpha$ radiation and a Ni filter. The d-spacings and intensities are shown in table C-1 for all samples analyzed. All of the samples appeared amorphous rather than crystalline and the manganese tended to cause some interference providing significant background to the resulting patterns.

Comparison of the d-spacings with strong and medium intensities for the first $LiMnF_5$ samples reveals that practically all appear among two or more of the samples analyzed. Preparation No. 14 may be Li_2MnF_6 as there is considerable correspondence between the d-spacings of the stronger intensities and those calculated for Li_2MnF_6 from the structure determination by Hoppe, et al.[31] The d-spacings for the $MnCl_2-BrF_3$ reaction product No. 12 are certainly different than the Li_2MnF_6 and $LiMnF_5$ spacings.

TABLE C-1. X-RAY DIFFRACTION POWDER PATTERNS OF LiMnF$_5$ PREPARATIONS

Line No.	Experimental LiMnF$_5$ No. 1 (Rust)		Experimental LiMnF$_5$ No. 3 (Gold)		Experimental LiMnF$_5$ No. 9		Experimental LiMnF$_5$ No. 10	
	d Spacing	Intensity	d Spacing	Intensity	d Spacing	Intensity	d Spacing	Intensity
1	6.2	s	6.2	w	6.0	m	4.3	vw
2	4.7	w	4.15	w	4.1	vw	3.75	vw
3	4.4	w	3.80	s	3.75	m	3.38	s
4	4.1	w	3.70	vw	3.40	w	2.75	vw
5	3.78	m	3.45	m	3.20	s	2.21	m
6	3.41	m	3.25	m	2.7	vw	2.10	m
7	3.20	m	2.72	w	2.35	vw	1.80	w
8	2.75	vw	2.38	w	2.20	vw	1.71	m
9	2.50	vw	2.20	w	2.10	s	1.65	w
10	2.37	m	2.10	m	2.00	vw	1.45	w
11	2.21	m	2.00	—	1.90	w	1.39	m
12	2.10	m	1.88	vw	1.81	m	1.33	w
13	1.90	w	1.80	m	1.71	w	1.20	vvw
14	1.81	m	1.70	vw	1.64	m	0.985	vvw
15	1.69	w	1.64	m	1.55	vw	0.941	vvw
16			1.365	w				
17			1.275	w				

TABLE C-1. (continued)

Line No.	Experimental LiMnF$_5$ No. 11 d Spacing	Intensity	Experimental MnF$_4$ No. 14 (MnF$_5$)$_4$ d Spacing	Intensity	Experimental MnCl$_2$ (Alpha Ventron-as received) d Spacing	Intensity	MnCl$_2$ ASTM Index d Spacing
1	5.9	w	4.9	s	5.85	s	5.85
2	4.2	w	4.3	m	3.15	w	3.16
3	3.79	m	3.7	m			3.01
					2.95	vs	2.99
4	3.41	s	3.2	m+	2.58	s	2.592
5	3.20	w	2.65	w	2.37	vw	2.371
6	2.65	w	2.20	w	1.98	vw	1.977
7	2.40	vw	1.86	w	1.85	m	1.95
							1.853
8	2.10	m	1.65	w	1.81	vw	1.812
9	1.81	m	1.48	w	1.76	w	1.766
10	1.72	w			1.50	vw	1.507
11	1.64	m			1.46	vw	1.464
12	1.54	vvw			1.29	vw	1.29
13	1.47	vvw			1.16	w	1.171
14					1.14	w	1.15
15					1.065	w	1.062
16					0.92	w	

Note: vs = very strong, s = strong, m = medium, w = weak, vw = very weak, vvw = very, very weak.